



# **Sulfidation of Ni-bearing goethites to pyrite: The effects of Ni and implications for its migration between iron phases**

Zhongkuan Wu, Tingting Zhang, Bruno Lanson, Hui Yin, Dong Cheng, Peng Liu, Feng He

## **► To cite this version:**

Zhongkuan Wu, Tingting Zhang, Bruno Lanson, Hui Yin, Dong Cheng, et al.. Sulfidation of Ni-bearing goethites to pyrite: The effects of Ni and implications for its migration between iron phases. *Geochimica et Cosmochimica Acta*, 2023, 353, pp.158-170. <10.1016/j.gca.2023.06.001>. <insu-04235259>

**HAL Id: insu-04235259**

**<https://insu.hal.science/insu-04235259v1>**

Submitted on 20 Oct 2024

**HAL** is a multi-disciplinary open access archive for the deposit and dissemination of scientific research documents, whether they are published or not. The documents may come from teaching and research institutions in France or abroad, or from public or private research centers.

L'archive ouverte pluridisciplinaire **HAL**, est destinée au dépôt et à la diffusion de documents scientifiques de niveau recherche, publiés ou non, émanant des établissements d'enseignement et de recherche français ou étrangers, des laboratoires publics ou privés.



HAL Authorization

**Sulfidation of Ni-bearing goethites to pyrite: the effects of Ni  
and implications for its migration between iron phases**

Zhongkuan Wu<sup>a</sup>, Tingting Zhang<sup>a</sup>, Bruno Lanson<sup>b</sup>, Hui Yin<sup>c</sup>, Dong  
Cheng<sup>a</sup>, Peng Liu<sup>d</sup>, Feng He<sup>a,e,\*</sup>

<sup>a</sup>*College of Environment, Zhejiang University of Technology, Hangzhou 310014,  
China*

<sup>b</sup>*Univ. Grenoble Alpes, Univ. Savoie Mont Blanc, CNRS, IRD, Univ. Gustave Eiffel,  
ISTerre, F-38000 Grenoble, France*

<sup>c</sup>*Key Laboratory of Arable Land Conservation (Middle and Lower Reaches of Yangtse  
River), Ministry of Agriculture and Rural Affairs, College of Resources and  
Environment, Huazhong Agricultural University, Wuhan 430070, China*

<sup>d</sup>*School of Environmental Studies & State Key Laboratory of Biogeology and  
Environmental Geology, China University of Geosciences, Wuhan 430074, China*

<sup>e</sup>*Environment and Civil Engineering, Jiangnan University, Wuxi, Jiangsu, 214122,  
China*

Corresponding author.

E-mail address: [fenghe@zjut.edu.cn](mailto:fenghe@zjut.edu.cn) (Feng He).

## ABSTRACT

Goethite and pyrite are common iron minerals in oxic or anoxic environments, respectively, both minerals being major reservoirs for Nickel, a bio-essential element. Mineral transformation between goethite and pyrite is frequent owing to the alternation of oxic and anoxic conditions in sulfate-rich environments. This mineral transformation has been amply studied, but the effect of Ni on this transformation and its fate along it remain poorly understood. Sulfidation of Ni-free and Ni-containing (through adsorption or isomorphic substitution) goethites was thus studied experimentally by reacting goethite with dissolved S(-II) (molar Fe:S $\approx$ 1:1). X-ray diffraction and associated Rietveld refinement, thermogravimetric analysis, scanning/transmission electron microscopy, X-ray absorption spectroscopy, and wet chemistry were used to monitor mineralogical evolutions and unravel Ni association with reaction products. After 44 days of sulfidation, about half of initial goethite converted to iron sulfides: thermodynamically stable pyrite (67%-93%) with minor contents of mackinawite (2%-15%) and greigite (5%-25%). Although the overall content of iron sulfides formed was essentially independent of Ni presence, Ni hampered the conversion from metastable iron sulfides (i.e., mackinawite and greigite) to pyrite (67%-78% vs. 93%, in the presence and absence of Ni, respectively). Pyrite formation from metastable sulfide precursors yielded a uniform Ni distribution in newly formed pyrite, regardless of the initial Ni association with goethite. Although no Ni was released to solution during pyrite formation, Ni incorporation to pyrite results in an increased risk of release to the environment as iron sulfides will be oxidized when exposed to air and water in supergene environments, leading to highly acidic conditions favoring Ni solubility and mobility.

**Keywords:** Nickel, Goethite, Sulfidation, Iron sulfides, Pyrite, Migration

## 1. Introduction

Laterite (Deoliveira et al., 1992; Dublet et al., 2015; Dublet et al., 2012; Fan and Gerson, 2015; Landers and Gilkes, 2007; Landers et al., 2009) and sulfide deposits (Ikogou et al., 2017; Morin et al., 2017; Noël et al., 2015; Swanner et al., 2019) represent the two most important Ni reservoirs in terrestrial environments (Elias, 2002). In both settings, goethite and pyrite are the two main host minerals for Ni. For example, goethite may present Ni-enrichment up to several weight percents (Dublet et al., 2012; Eliopoulos and Economou-Eliopoulos, 2000; Ugwu and Sherman, 2019) and commonly accounts for ~60-75% of the Ni pool in laterites (Fan and Gerson, 2015; Landers et al., 2009; Manceau et al., 2000). Goethite sequesters Ni, and other transition metals, via surface adsorption (Nachtegaal and Spark, 2002; Ugwu et al., 2019; Xu et al., 2006) and isomorphic substitutions (Cornell, 1991; de Carvalho-E-Silva et al., 2002; Dublet et al., 2015; Landers and Gilkes, 2007; Manceau et al., 2000). Ni(II) adsorbed to goethite surface is commonly considered to readily desorb, whereas incorporation in goethite crystal structure (Ugwu et al., 2019) results in a more stable sequestration. Both adsorbed and structurally incorporated Ni modify goethite's physicochemical properties, affecting its subsequent reactivity, including phase transformation. In particular, adsorbed Ni(II) was reported to compete with other adsorbents for goethite surface sites (Xu et al., 2006) and to delay goethite recrystallization (Friedrich et al., 2019). Ni(II)-for-Fe(III) substitutions also influence vibrational properties of surface hydroxyl groups (de Carvalho-E-Silva et al., 2002), surface charge, or solubility (Ugwu and Sherman, 2019) of goethite particles in particular owing to the difference in valence of Fe(III) and Ni(II) in goethite crystal structure (de Carvalho-E-Silva et al., 2002; Friedrich et al.; Gasser et al., 1996; Ugwu and Sherman, 2019; Zachara et al., 2001)

Although goethite is the most common and the thermodynamically most stable iron (oxyhydr)oxide on Earth (Cornell and Schwertmann, 2004), it may be altered under reducing conditions through interactions with microorganisms (Maurice et al., 2000; Zachara et al., 2001), organic compounds (Gasser et al., 1996; Larsen and Postma, 2001; Suter et al., 1991), or inorganic reductants (Poulton et al., 2004; Rickard, 1974; Suter

et al., 1991). As a result, goethite may be dissolved (Dos Santos Afonso and Stumm, 1992) or transformed to secondary Fe minerals such as iron sulfides (e.g. pyrite, mackinawite, etc.) as the result of its interaction with dissolved sulfides [including H<sub>2</sub>S, HS<sup>-</sup>, and S(-II), hereafter globally referred to as S(-II)] (Poulton et al., 2004; Rickard, 1974; Wan et al., 2017; Wang and Morse, 1996). Such reducing conditions are commonly found in flooded sulfate-rich farmlands, wetlands, and marshes, where S(-II) could accumulate up to ~15 mM as the result of microbial anaerobic respiration (Bagarinao, 1992). A wealth of literature has been devoted to deciphering the interaction of goethite and other iron (oxyhydr)oxides with S(-II), a process commonly referred to as sulfidation (Kumar et al., 2018; Poulton et al., 2004; Rickard and Luther, 2007; Rickard, 1974; Wan et al., 2017), iron (oxyhydr)oxides being regarded as the main iron suppliers for the early diagenetic formation of pyrite (Canfield, 1989). Goethite sulfidation is of particular importance as it is regarded as the starting point for sedimentary pyrite formation (Rickard, 1974), resulting in the association of goethite and pyrite under reducing (Seyfferth et al., 2020) or alternating oxidizing and reducing conditions (Otero et al., 2009). Mechanisms of goethite [or other iron (oxyhydr)oxides] sulfidation are well documented: first, S(-II) is adsorbed to the surface of the iron (oxyhydr)oxide allowing an electron-transfer from S(-II) to Fe(III) to form Fe(II), elemental sulfur (S<sup>0</sup>), and polysulfides (S<sub>n</sub><sup>2-</sup>) (Luther, 1991). S(-II) in excess then precipitates with Fe(II) to form amorphous FeS<sub>x</sub> clusters, that transform first to crystalline but metastable monosulfides (mackinawite) and then to greigite. A final reaction between metastable iron sulfides (MIS: mackinawite and greigite) and S<sup>0</sup>, S<sub>n</sub><sup>2-</sup>, or H<sub>2</sub>S produces thermodynamically stable pyrite (de Carvalho-E-Silva et al., 2002; Hurtgen et al., 1999; Lan and Butler, 2014; Luther, 1991; Pyzik and Sommer, 1981; Rickard and Luther, 2007; Schoonen and Barnes, 1991b; Wang and Morse, 1996).

In S(-II)-rich sediments, sulfidation of goethite and other Fe (oxyhydr)oxides is a typical process of reductive-dissolution and recrystallization (Luther, 1991; Wang and Morse, 1996), and as such strongly influences transport and bioavailability of foreign metals initially associated to goethite (Hockmann et al., 2020; Zachara et al., 2001). The sole reductive-dissolution of goethite and other iron (oxyhydr)oxides releases both

adsorbed [like As and Ni – (Huang et al., 2015; Ren et al., 2018)] and substituted [like Al, Co, Mn, Ni, Cr – (Dubbin and Bullough, 2017; Landers and Gilkes, 2007; Maurice et al., 2000)] foreign elements to aquatic systems. In particular, structurally incorporated Ni(II) may be released to the aqueous phase during a bacteria mediated (Zachara et al., 2001) or HCl caused (Landers and Gilkes, 2007) reductive-dissolution of goethite, or lost during the lateritization process (Dublet et al., 2015). In contrast, when reductive-dissolution occurs in the presence of S(-II), an efficient reducing species (Canfield, 1989; Canfield et al., 1992), this species can readily coprecipitate with both Fe(II) and Ni(II) (Morse and Luther, 1999) thus leading to the formation of solid metal sulfides. Interestingly, the fate of Ni along goethite sulfidation and its effect on this process remain sparingly documented although iron sulfides are also important Ni sinks in sediments (Ikogou et al., 2017; Noël et al., 2015).

To bridge this knowledge gap, the present study investigated experimentally the sulfidation of goethite containing adsorbed or isomorphically substituted Ni, to decipher Ni transfer from oxic laterite deposits to anoxic sulfide deposits. Both the mineralogical transformations and Ni retention were characterized using X-ray diffraction, electron microscopy, thermogravimetric analysis, X-ray absorption spectroscopy, and wet chemistry. The main goal of the present work was to elucidate the fate of both adsorbed and substituted Ni(II) species during goethite sulfidation and Ni influence on the process.

## 2. Experimental Methods

### 2.1. Goethite preparation

Ni-free goethite was prepared according to a modified version of Cornell and Schwertmann (2004) protocol. Briefly, 600 mL of a 0.167 M Fe(NO<sub>3</sub>)<sub>3</sub> solution was prepared from the dissolution of Fe(NO<sub>3</sub>)<sub>3</sub>·9H<sub>2</sub>O into MilliQ water (18.2 MΩ.cm) in a plastic beaker. Then, 180 mL of 5 M KOH was added in the above solution at a 5 mL/min rate with continuous stirring. The obtained suspension was then diluted to 2 L using MilliQ water, and let to settle down and age at room temperature for 7 days. The

resulting precipitate was subsequently washed with 400 mL oxalate/ammonium oxalate solution (pH=3) for 2 hrs to remove amorphous precipitates and adsorbed species, and dialyzed until conductivity was < 20  $\mu$ S/cm. The resulting paste was finally centrifuged, freeze-dried, ground, and sieved (100 mesh). Ni-incorporated goethites were synthesized along the same protocol but using mixed  $\text{Fe}(\text{NO}_3)_3$  and  $\text{Ni}(\text{NO}_3)_2$  solutions with Ni/(Ni+Fe) molar ratios of 0.02 or 0.06 (Ugwu and Sherman, 2019). Resulting samples are hereafter referred to as Gt, GtNi2, and GtNi6, according to the initial Ni contents.

Additional Ni-bearing goethite samples were obtained from sorption experiments: 150 mL of a 0.01 M (or 0.04 M)  $\text{Ni}(\text{NO}_3)_2$  solution were added to 150 mL of a 10 g/L Gt suspension, the mixed solution being stirred for 24 hrs. Both Gt suspension and  $\text{Ni}(\text{NO}_3)_2$  solution were prepared using a 0.01 M  $\text{NaNO}_3$  ionic background. Before mixing, the suspension pH was adjusted to 6.00 and allowed to vary by less than  $\pm 0.05$  pH units for 12 hrs. The final suspension was centrifuged and washed twice, before being freeze-dried. Resulting solids are hereafter referred to as GtANi5 (GtANi20).

The relative contents of Fe and Ni for Ni-containing goethites were determined by dissolving 10 mg of solids into 10.00 mL of 6 M HCl solution in duplicates, and metal concentration was measured via Atomic Absorption Spectroscopy (AAS). Results are shown in Table 1.

**Table 1**

Relative content of Ni and Fe in synthetic goethites.

Samples	$c_{\text{Fe}}$ (mg/g)	$c_{\text{Ni}}$ (mg/g)	Ni/(Fe+Ni) at. %
GtNi2	572.1 $\pm$ 3.3	6.66 $\pm$ 0.11	1.1
GtNi6	557.1 $\pm$ 1.7	13.26 $\pm$ 0.05	2.2
GtANi5	573.8 $\pm$ 3.5	6.56 $\pm$ 0.05	1.1
GtANi20	566.9 $\pm$ 3.4	9.12 $\pm$ 0.02	1.5

## 2.2 Sulfidation experiments

Goethite sulfidation experiments were performed in a glovebox [(Mikrouna, 100% Ar), maintained at < 1 ppm (v/v)  $\text{O}_2$  using a copper catalyst] at room temperature ( $\sim 23^\circ\text{C}$ ) using a protocol similar to that of previous studies (Hockmann et al., 2020; Wan et

al., 2017). Reagents and MilliQ water used in this part were purged with N<sub>2</sub> for more than 4 hrs before being transferred to the glovebox to minimize O<sub>2</sub> content of reacting solutions/suspensions prepared in the glovebox. 1.00 g of Gt, GtNi<sub>2</sub>, GtNi<sub>6</sub>, GtANi<sub>5</sub>, and GtANi<sub>20</sub> were then added to 1 L of a 11.24 mmol Na<sub>2</sub>S solution (Fe:S molar ratio ≈1), whose pH was adjusted to 6.00±0.10 using HCl and maintained for 12 hrs before goethite addition. Each set was gently stirred with a magnetic stirrer for several mins every day, and the pH was monitored and adjusted manually with HCl or NaOH as needed.

At certain time intervals, aliquots were withdrawn for analysis of aqueous and/or solid phases. Aqueous samples were filtered through 0.22 µm nylon membrane (the filtration may be repeated up to 8 times until the solution got colorless due to the formation of colloidal FeS at the beginning of the sulfidation) before further measurement. Ni concentration in solution was determined with AAS, that of Fe(II) with the phenanthroline method (Fadrus and Malý, 1975), and that of dissolved sulfides via the methylene blue method (Cline, 1969; Hockmann et al., 2020). Solid samples were retrieved by centrifugation and subsequently dried in the glovebox for several days. They are named as *Sample\_name-Reaction\_time*; for example, Gt-44d was obtained from Gt reacting with S(-II) for 44 days. Elemental sulfur (S<sup>0</sup>) present on the surface of sulfidized solids was measured using a methanol extraction method: 7.0 mg of solids were added to 7.00 mL of methanol, the mixture being then sonicated for 10 mins, and S<sup>0</sup> content being then determined using high-performance liquid chromatography (Agilent-1260).

## 2.3 Characterization of goethites and of their sulfidized products

Mineralogy of Ni-free/-bearing goethites, and of their sulfidized counterparts was determined by X-ray diffraction (XRD), using a Bruker D8 Advance diffractometer equipped with a Cu K $\alpha$  source ( $\lambda = 1.5418$  Å, voltage 40 kV, current 40 mA), and using a scanning rate of 1 °/min and 0.02 ° step size. Quantitative phase analysis of sulfidized samples was performed through the Rietveld refinement of XRD data using the Profex software (Döbelin, 2015; Döbelin and Kleeberg, 2015). Thermogravimetric analysis



(TGA, Mettler) was performed from room temperature to 800 °C at a heating rate of 10 °C/min and under a continuous N<sub>2</sub> flow of 20 mL/min. Scanning electron microscopy (SEM) observations were performed on a Zeiss Sigma300 instrument operated with an accelerating voltage of 30 kV and a working distance of 50 mm. Transmission electron microscopy (TEM) investigations were performed on a FEI Tecnai G2 F30 microscope operated at 300 kV. STEM-HAADF (scanning transmission electron microscopy – high-angle annular dark field) images were obtained using Bruker Super Lite X2.

Fe K-edge extended X-ray absorption fine structure (EXAFS) spectra were recorded at the 4B9A beamline of the Beijing Synchrotron Radiation Facility (BSRF). A metallic Fe foil ( $E_0=7112$  eV) was systematically used for energy calibration before data collection; data was collected at room temperature and in transmission mode over the 6920–7920 eV range. Data reduction was performed using Athena (Ravel and Newville, 2005). Fourier transform (FT) of  $k^3$ -weighted  $\chi(k)$  data was performed over the 2.9–12.2 Å<sup>-1</sup>  $k$ -range to obtain the radial distribution function (RDF)  $\chi(r)$  in real space.

## 2.4 Acid dissolution

From the literature, goethite ( $\alpha$ -FeOOH), mackinawite [(Fe,Ni)<sub>1+x</sub>S], and greigite [Fe(II)Fe(III)<sub>2</sub>S<sub>4</sub>] are readily soluble in (hot) HCl. Pyrite does not usually dissolve in HCl (Cooper and Morse, 1998; Cornwell and Morse, 1987; Morse et al., 1987), although nanocrystallinity may allow pyrite dissolution in HCl (Cooper and Morse, 1998; Cornwell and Morse, 1987; Morse et al., 1987), but is readily dissolved in HNO<sub>3</sub>. A HCl-HNO<sub>3</sub> sequential treatment was thus modified from that of Huerta-Diaz and Morse (1990) to determine the association of Ni with iron oxides/sulfides according to their Fe/Ni release behavior. Specifically, 100 mg of sulfidized samples were added to 100 mL of 3 M HCl in a capped conical flask and kept at 40 °C using a water bath. Magnetic stirring could not be used owing to the highly magnetic character of sulfidized solids, and flasks were thus shaken for 5 mins to homogenize the solution every day and before each sampling. After 4 days in HCl, goethite, mackinawite, and greigite were supposed to be fully dissolved, with only pyrite being left. The residual solid was


then filtered and washed twice, before being transferred in 45 mL of 2 M HNO<sub>3</sub>. During both acid treatments, aliquots were sampled at different time intervals to determine Fe and Ni concentrations using AAS. After ~120 hrs of treatment in 2 M HNO<sub>3</sub>, solids could still be observed, which could be dissolved completely by adding 10 mL of aqua regia.

### 3. Results

#### 3.1. Powder X-ray diffraction

Synthesized Ni-free Gt yielded a diffraction pattern typical for goethite (Fig. 1, ICDD#29-0713). XRD patterns of Ni-bearing goethites were essentially similar to that of Gt, without additional diffraction lines, indicating Ni incorporation in goethite crystal structure or sorption at its surface. After reacting with S(-II) under anoxic conditions for 3 days, XRD patterns of reacted samples were similar to those of their unreacted counterparts, whereas modifications were visible from 7 days of reaction and on (Fig. S1). XRD patterns of Ni-free and Ni-bearing samples were dominated by peaks at ~21.2°/~36.6° (2θ – goethite 110 and 111 reflections – Fig. 1), whereas after sulfidation the peak at ~33.1° (2θ – pyrite 200 reflection) became most intense for all samples. Consistently, intensities of goethite peaks at ~53.3°, ~59.1°, ~61.4°, and ~64.0° (2θ – goethite 221, 151/160, 002, and 061 reflections, respectively) significantly decreased with increasing reaction time. In addition, peaks at ~36.6°, ~47.3°, ~59.1°, and ~61.4° (2θ) shifted to higher angles (green arrows in Fig. 1), and the peak at ~36.6° (2θ) was split on its high-angle side (blue arrow in Fig. 1). These evolutions indicated the formation of new phase(s) at the expense of goethite. Additional reflections at ~28.5° and ~56.3° (2θ) were attributed to pyrite (111 and 311 reflections, respectively - ICDD#42-1340), those at ~30.1°, ~39.0°, and ~49.6° (2θ) to mackinawite (101, 111, and 200 reflections, respectively - ICDD#15-0037), whereas weak peaks at ~25.4° and ~52.4° (2θ) indicated the presence of greigite (220 and 440 reflections, respectively - ICDD#16-0713) in reaction products, consistent with previous reports of goethite sulfidation (Wang and Morse, 1996). No nickel sulfides, other iron (oxyhydr)oxides, or


elemental sulfur ( $S^0$ ) were detected using XRD, although the latter was reported in similar studies (Hockmann et al., 2020; Rickard, 1974).

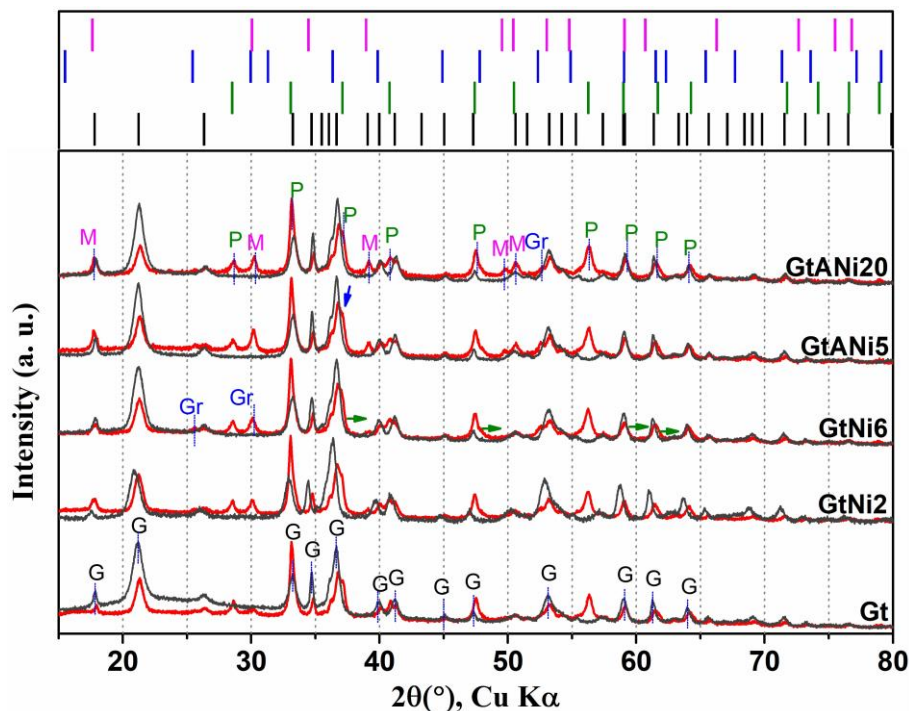

**Fig. 1** Powder XRD patterns obtained from pristine Ni-free/-containing goethites (black) and from the corresponding reaction products after 44 days of interaction with S(-II) (red). G=goethite, P=pyrite, Gr=greigite, and M=mackinawite. Bars, from bottom to top, above these patterns are characteristic diffraction lines for: goethite (ICDD#29-0713; black), pyrite (ICDD#42-1340; green), greigite (ICDD#16-0713; blue), and mackinawite (ICDD#15-0037; magenta).

Quantitative phase analysis was performed using the Rietveld method to quantify the contributions of the four Fe-bearing minerals identified in sulfidized samples (Fig. 2, Table S1) in an effort to monitor sulfidation progress. Colloidal FeS and FeS<sub>x</sub> clusters remain undetected by this approach however. After 3 days of reaction, minor amounts (~1-2%) of iron sulfide minerals were detected in all runs. After 7 days, ~40% of initial Gt and GtNi6 was converted to iron sulfides, mainly pyrite, that is more than that in GtANi5-7d and GtANi20-7d (~32%), possibly because the pre-existing sorption of Ni(II) to the goethite surface (Hellige et al., 2012; Hockmann et al., 2020; Wan et al., 2017) hindered the interaction of S(-II) with structural Fe(III) during the early stages of GtANi5 and GtANi20 sulfidation, consistent with previous reports (Biber et al., 1994; Poulton et al., 2004). Goethite sulfidation then proceeded, with about half of initial goethite being transformed to sulfides after 44 days of reaction. For example, sulfide

278 content was ~59% in Gt-44d (Table S1), a content significantly higher than that in  
 279 sulfidized Ni-bearing goethites (~46-52%, Table S1), suggesting that the association of  
 280 Ni incorporated in or adsorbed to goethite significantly hampered its conversion to iron  
 281 sulfides. For all samples, pyrite was the main crystalline product of goethite sulfidation  
 282 (~33%-54%) (Rickard, 1974), with a minor contribution of greigite (~3%-12%) and  
 283 mackinawite (~1%-8%), the latter two being commonly considered as pyrite precursors  
 284 (Luther, 1991; Rickard and Luther, 2007). Consistently, the overall content of  
 285 metastable iron sulfides (MIS: mackinawite, greigite) remained limited in all reacted  
 286 samples, suggesting that pyrite was formed at the expense of MIS or that MIS formation  
 287 was inhibited. In addition, MIS appeared less abundant in Gt reaction products  
 288 compared to Ni-bearing goethite reaction products.

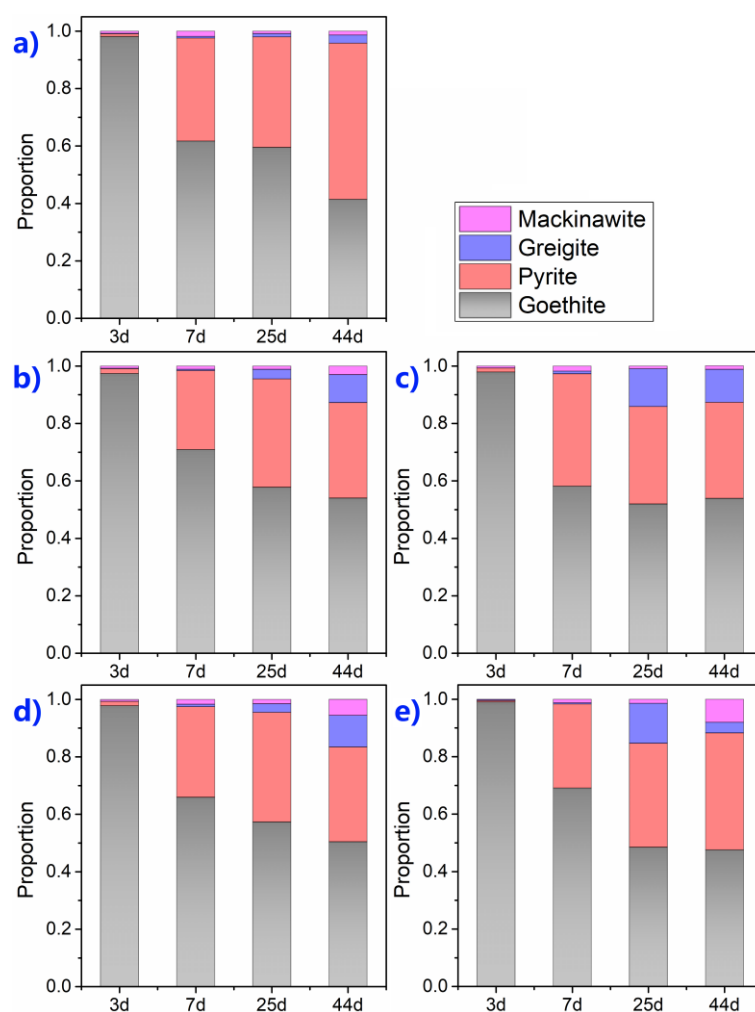

289

290 **Fig. 2.** Evolution as a function of reaction time of the mineralogy of reaction products of Ni-free/-  
 291 containing goethites after their interaction with S(-II): a): Gt, b): GtNi2, c): GtNi6, d): GtANi5, and


e): GtANi20. Errors on mineral fractions are given in Table S1.

Incorporation of Ni in goethite led to a minor distortion of its crystal framework, and more especially to a slight expansion of its b unit-cell parameter from 9.957(6) to 9.966(8) Å, a and c unit-cell parameters remaining essentially unchanged (Table S2), consistent with previous reports (Wells et al., 2006). By contrast, unit-cell parameters of the two Ni-adsorbed samples are logically almost identical to those of Gt. After 44 days of sulfidation, the low contents of greigite and mackinawite generate large uncertainties on their unit-cell parameters precluding an unambiguous assessment of their evolution. Unit-cell parameters of pyrite formed both from Ni-free and Ni-bearing goethites are identical within uncertainty.

### 3.2. Evolution of Fe local environments

Consistent with the above-described mineralogical evolution along goethite sulfidation, Fe local environment was modified as shown by the evolution of Fe K-edge EXAFS spectra (Fig. S2) and of corresponding RDFs (Fig. 3). It was not possible to determine relative proportions of the different Fe-bearing phases from linear combination fitting of the EXAFS spectra however. All attempts to fit EXAFS data using reference spectra of colloidal FeS (Nöel et al., 2020), mackinawite, greigite, pyrite, and goethite did not allow reaching a satisfactory fit (not shown), thus precluding comparison with the mineralogy determined from Rietveld refinement of the XRD data (Table S1, Fig. S1). The inability to fit the EXAFS signature of the solid fraction is likely related to contrasting signatures of FeS<sub>x</sub> clusters present in the solid fraction and of the colloidal FeS reference that was obtained from filtered (<0.02 µm) solutions by Nöel et al.(2020) as suggested by the mismatch between the spectral signature of colloidal FeS and the modification of EXAFS spectra after 3 days of sulfidation (Figs. S2 and S3). In both k- and r-space, pristine samples data was typical of goethite (Burton et al., 2010; Hohmann et al., 2011), with a first maximum at ~1.50 Å (R+ΔR) in r-space corresponding to the first Fe-O shell and an asymmetric peak spanning from ~2.30 to ~3.60 Å (R+ΔR), peaking at ~2.70 Å (R+ΔR), and corresponding to Fe-Fe bonds in goethite edge- and corner-sharing FeO<sub>6</sub> octahedra. After reacting for 3 days with S(-II),

the frequencies of goethite EXAFS spectra in k-space were essentially alike those of pristine samples. Amplitudes were attenuated however (Fig. S2), the modification being most significant for Gt relative to Ni-bearing goethites (Fig. S3), suggesting a negative effect of Ni on goethite sulfidation. Consistently, the Fe-Fe shell at  $\sim 2.70$  Å (R+ΔR) in r-space decreased slightly (Fig. 3), supporting a minor decrease in the number of edge-sharing linkages between FeO<sub>6</sub> octahedra in goethite. In addition, the minor increase of the shoulder at  $\sim 1.80$  Å (R+ΔR) (Fig. 3) supports the early formation of Fe-S bonds, consistent with the formation of FeS<sub>x</sub> clusters. After 7-44 days of sulfidation, Fe K-edge spectra were strongly modified compared to that of pristine samples with a major evolution of frequencies in k-space (Figs. S2 and S3). Consistently, the main contribution to the first coordination shell of Fe shifted from  $\sim 1.50$  Å to  $\sim 1.80$  Å (R+ΔR); similarly, the asymmetric peak extending from  $\sim 2.30$  to  $\sim 3.60$  Å (R+ΔR) with a maximum at  $\sim 2.70$  Å (R+ΔR) in pristine samples weakened and split into two isolated peaks of similar intensity at  $\sim 2.80$  Å and  $\sim 3.40$  Å (R+ΔR). The peak at  $\sim 2.80$  Å combines the contributions from edge-sharing Fe-Fe linkages of FeO<sub>6</sub> octahedra in goethite and from Fe-S<sub>2nd</sub> linkages in pyrite, whereas that at  $\sim 3.40$  Å (R+ΔR) is related to the nearest Fe-Fe shell in pyrite (corner-sharing linkages of FeS<sub>n</sub> polyhedra). These modifications are consistent with the conversion of a significant fraction of goethite to iron sulfides after 44 days of sulfidation, most of the conversion occurring from 3 to 7 days of sulfidation, consistent with XRD results (Figs. 1, 2, and S1, and Table S1). On the difference plots between reacted and initial samples (Fig. S3), reacted Gt samples systematically showed significantly stronger differences (both after 3 and 44 days of sulfidation), compared to GtNi6 and GtANi20 supporting the negative effect of Ni association to goethite on its sulfidation.

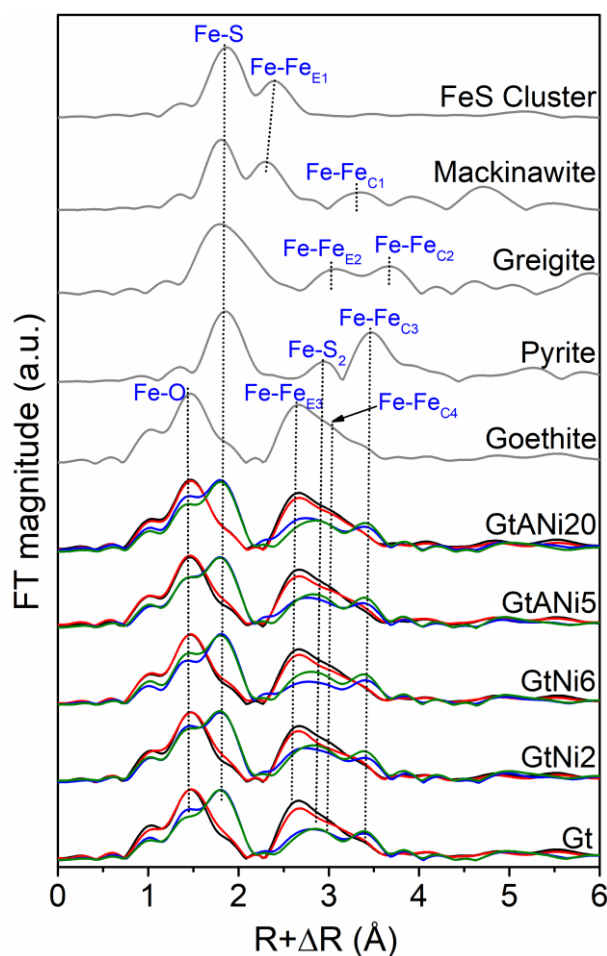

**Fig. 3.** Fourier transforms of Fe K-edge EXAFS spectra obtained for pristine (black) and sulfidized goethite samples (red: 3 days, blue: 7 days, green: 44 days), and iron oxhydroxide/sulfide standards (gray). To highlight the evolution of Fe local environment, FT intensities were normalized to that of the first shell. Data for colloidal FeS from Noël et al. (2020). Fourier transform for greigite was computed from the Fe K-edge EXAFS spectrum calculated with Feff8.4 based on greigite structure model (COD#9000123 – Ikogou et al., 2017). For mackinawite, Fe-Fe<sub>E1</sub> and Fe-Fe<sub>C1</sub> indicate edge- and corner-sharing linkages of FeS<sub>4</sub>-FeS<sub>4</sub> tetrahedra; for greigite, Fe-Fe<sub>E2</sub> and Fe-Fe<sub>C2</sub> indicate edge- and corner-sharing linkages between FeS<sub>6</sub>-FeS<sub>6</sub> octahedra and FeS<sub>4</sub>/FeS<sub>6</sub>-FeS<sub>6</sub> polyhedra, respectively; for pyrite, Fe-S<sub>2</sub> and Fe-Fe<sub>C3</sub> indicate the second nearest Fe-S shell and corner-sharing linkages of FeS<sub>6</sub> octahedra, respectively; for goethite, Fe-Fe<sub>E3</sub> and Fe-Fe<sub>C4</sub> indicate edge- and corner-sharing linkages of FeO<sub>6</sub>-FeO<sub>6</sub> octahedra, respectively.


### 3.3. Thermogravimetric analysis

Consistent with the observed mineralogical evolution upon goethite sulfidation, the thermogravimetric analysis of unreacted and reacted samples differed significantly (Fig. 4). All goethite samples (with or without Ni) exhibited a significant weight loss from ~170 °C to ~300 °C with a maximum at ~255 °C typical for goethite dehydroxylation and conversion to hematite [ $\alpha$ -Fe<sub>2</sub>O<sub>3</sub> – (Cornell and Schwertmann, 2004; Ponomar,



2018)]. Weight losses occurring prior to dehydroxylation were ascribed to the loss of physisorbed water. An additional weight loss was observed at ~300 °C for GtANi20 (Fig. 4e), which is possibly related to the presence of adsorbed Ni(II) on goethite surface. Compared to pristine samples, goethite dehydroxylation weight loss was still observed in sulfidized samples, consistent with the presence of unreacted goethite, but shifted to slightly higher temperature (~270 °C) compared to unreacted samples. In addition, the splitting of TGA data first derivative observed over this low-temperature range (Figs. 4b,d) suggests the contribution of another process to the weight loss of sulfidized samples. The temperature shift of goethite dehydroxylation weight loss could correspond to a morphological/size evolution of unreacted goethite whereas the additional process possibly results from the partial conversion of greigite (Krs et al., 1993; Kyprianidou-Leodidou et al., 1997; Sagnotti and Winkler, 1999). For all sulfidized goethites, two major weight losses were observed at ~510-525 °C and ~555-570 °C (Fig. 4) that are typical for pyrite (Yang et al., 2019). Two additional weight losses were observed at low temperatures (~215/220 °C and ~240/245 °C) in sulfidized Ni-containing goethites. These weight losses are possibly related to the presence of Ni- or Ni-rich phases [possibly  $\text{Ni}_{1-x}\text{S}$  – (Bishop et al., 1999)] as they were not observed for sulfidized Ni-free Gt and did not appear to be related to the presence of a specific Fe sulfide species. These Ni-rich phases were not detected using XRD however. Another weight loss was observed at 390/415 °C in the TGA curves of sulfidized Ni-bearing goethites (Figs. 4d,f), but was absent in the reacted Ni-free Gt (Gt-16d/44d). This weight loss is possibly ascribed to the decomposition of  $\text{NiS}_2$  to NiS (Dunn and Kelly, 1977).



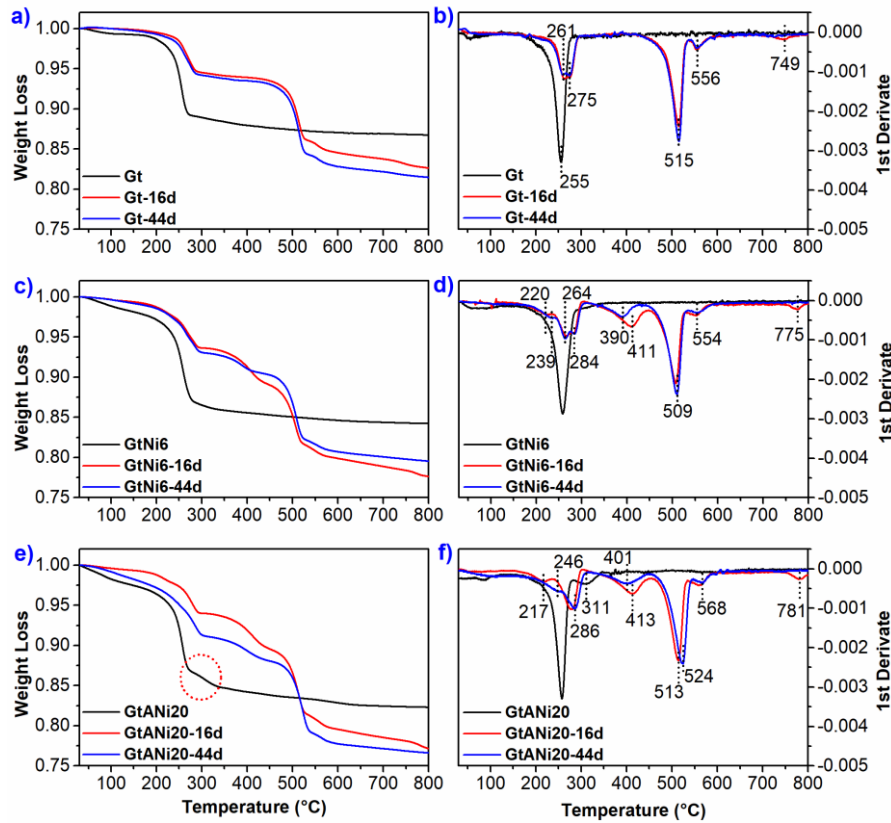


**Fig. 4.** Experimental thermogravimetric curves (left) and their first derivatives (right) for pristine (black) and sulfidized goethite samples (red: 16 days, blue: 44 days): a,b) Gt; c,d) GtNi6; e,f) GtANI20.

### 3.4. Electron microscopy

Goethite sulfidation and the associated crystallization of Fe-rich sulfides (pyrite, greigite, mackinawite) were associated with a dramatic morphological evolution (Figs. 5 and S4). All pristine goethite samples were acicular shaped with lath lengths ranging ~300-400 nm or more, typical for goethite (Cornell and Schwertmann, 2004), and no significant difference was detected between Gt and Ni-bearing samples. Crystal habits were more heterogeneous in sulfidized samples with three main crystal habits: i) laths extending ~100-300 nm in length and corresponding to residual goethite after their interaction with S(-II); ii) framboids extending several hundred nanometers in diameter and composed of cubic pyrite nanocrystals (Wang and Morse, 1996); iii) irregular lamellas, possibly corresponding to greigite as suggested by lattice fringes exhibiting ~0.350 and 0.285 nm periodicities [greigite (220) and (222) planes; Fig. S4f,i – (Cao et al., 2009; Islam and Patel, 2017; Lan and Butler, 2014)]. Although Rietveld refinement

indicated that half of the initial goethite was preserved in sulfidized samples (Table S1), the framboids and irregular lamellas visually dominated the three sulfidized samples, suggesting that residual goethite might be covered by newly formed iron sulfides. Contrasting with micrometer-sized cubic/polyhedral pyrite crystals reported previously (Butler and Rickard, 2000; Du et al., 2021; Liu et al., 2022; Lowers et al., 2007), pyrite grain sizes ranged from tens to hundreds of nanometers in the present sulfidized goethites. Consistent with previous TEM observations (Kumar et al., 2018; Peiffer et al., 2015), no joints between pyrite framboids and goethite laths were observed, thus confirming that the goethite-to-iron sulfides transformation proceeded mainly through dissolution-recrystallization (Wang and Morse, 1996), rather than as a solid-state conversion.


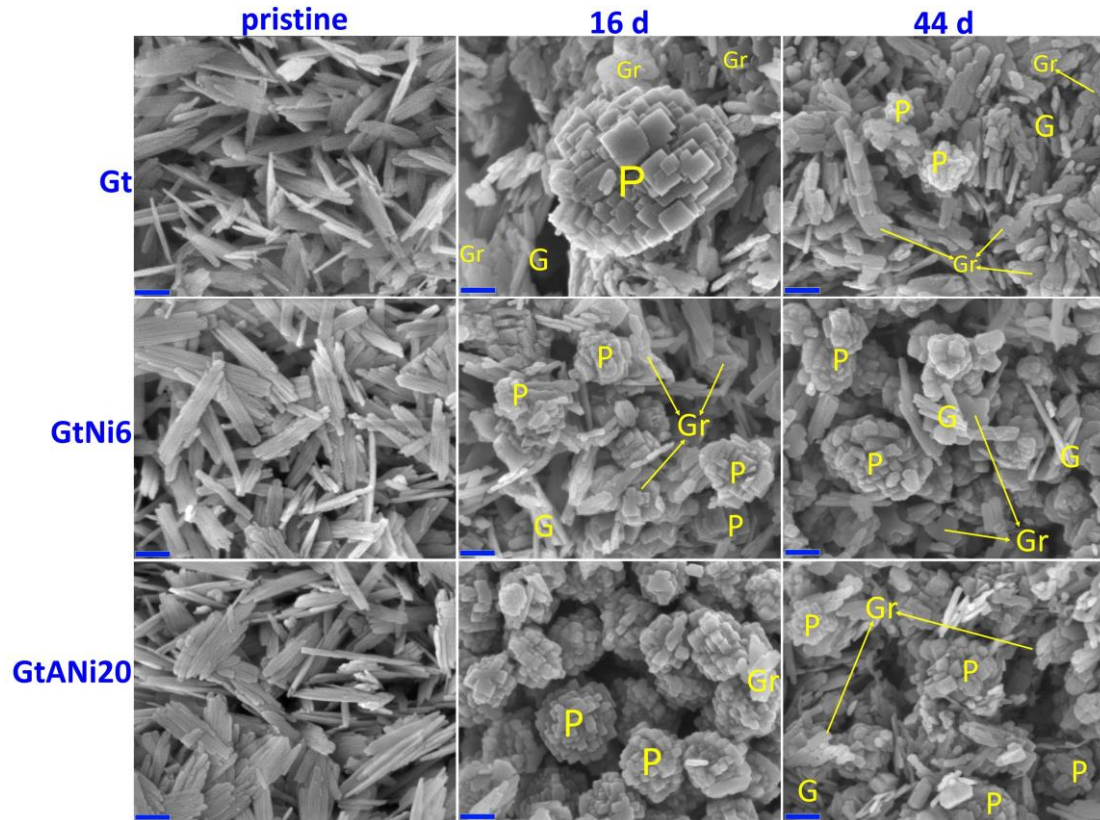


**Fig. 5.** Scanning electron micrographs of pristine and sulfidized Ni-free/-bearing goethites. G, P, Gr, and M stand for goethite, pyrite, greigite, and mackinawite, respectively. Blue scale bars at the lower left of each figure represent 100 nm.

### 3.5. Solution chemistry during sulfidation (S(-II) and Fe(II)

#### concentrations)

S(-II) concentration in solution decreased dramatically below the detection limit of the methylene blue method (0.02 mg/L) within 3 days (Fig. 6a). S(-II) consumption rate was similar for all goethite samples. This decrease resulted from the quick adsorption of S(-II) to goethite surface and from the subsequent swift formation of amorphous FeS<sub>x</sub> clusters induced by S(-II) interactions with Fe(II) (Poulton, 2003; Wan et al., 2017) according to:



Consistently, Fe(II) and elemental sulfur (S<sup>0</sup>) were produced as the result of these interactions immediately after adding goethite to the S(-II) solution (Figs. 6b,c). After an initial steady increase, Fe(II) content in solution stabilized after ~15 days of sulfidation, most likely because Fe(II) consumption related to Fe sulfides formation compensated its production according to Eq. 1, and to the subsequent destabilization of both FeS<sub>x</sub> clusters / colloidal FeS and MIS. After a possible sharp initial increase (not detected), S<sup>0</sup> amount decreased gradually in the system most likely as the result of pyrite formation from Fe sulfide precursors according to Eq. 3 (Rickard, 1975). Consistent with quantitative phase analysis, pyrite formation was most noticeable over 3-7 days in all experiments (Table S1, Fig. 6c). Ni concentration in solution was systematically lower than its detection limit with AAS (0.05 mg/L – data not shown).


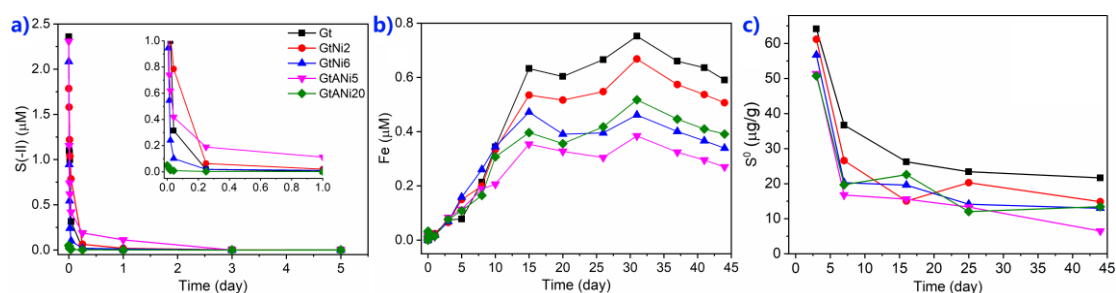


Fig. 6. Evolution of (a) S(-II) and (b) Fe(II) concentration in solution and (c) relative mass of

elemental sulfur ( $S^0$ ) associated with the solids as a function of sulfidation time for Ni-free/-bearing goethites.  $S^0$  content was quantified only for sulfidized samples.

### 3.6. Solid chemistry during sulfidation

Content and distribution of Fe, Ni, O, and S within sulfidized particles were determined using HAADF imaging coupled with EDX analysis (Figs. 7 and S5). Fibrous morphologies were ascribed to goethite crystals, whereas bright areas in HAADF dark field micrograph were mainly related to aggregated crystals shown in Figs. 5 and S5 and identified as iron sulfides, consistent with elemental distributions. Both Fe and O were evenly distributed in both types of crystals however, consistent with the formation of Fe sulfides on residual goethite particles. On the other hand, Ni and S appeared to be concentrated in the bright areas, the distributions of the two elements being highly correlated, indicative of the slight Ni enrichment of newly formed iron sulfides compared to residual goethite. For example, Ni mass fraction in selected Fe sulfide polycrystals and goethite crystals (areas #1 and #2, respectively, in Fig. 7 upper left) were  $0.9 \pm 0.3\%$ , and  $0.5 \pm 0.2\%$ , respectively.

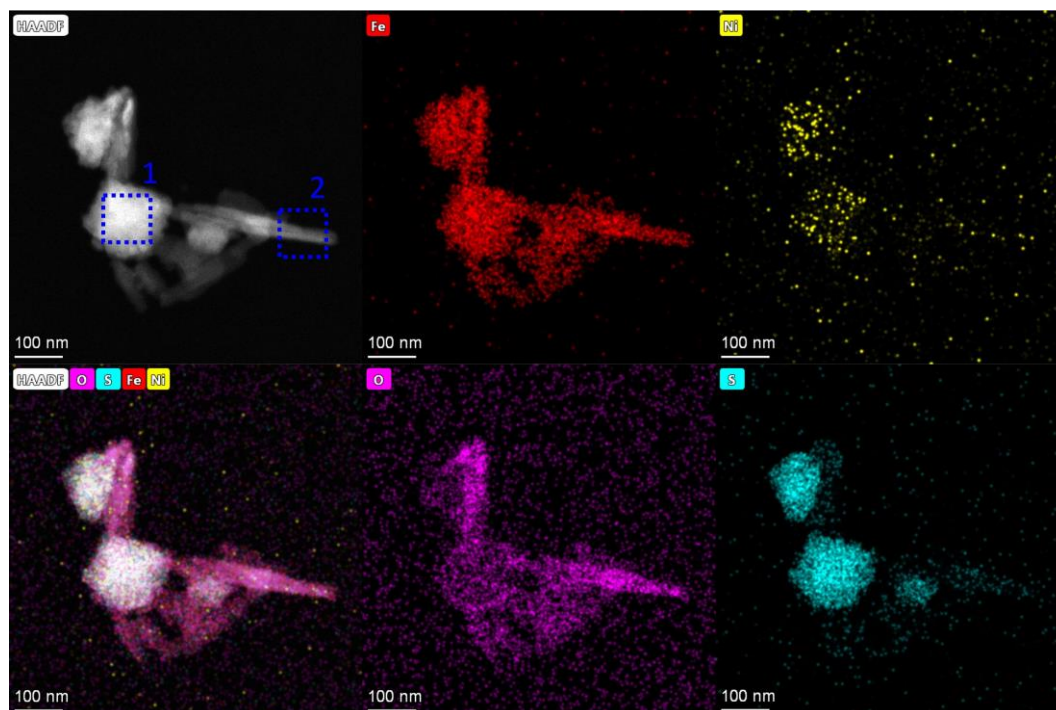

**Fig. 7.** STEM/HAADF micrograph (upper left) and EDX maps for Fe (upper center), Ni (upper right), O (lower center), S (lower right), and composite Fe-Ni-S-O image obtained for GtANi20-44d.

### 3.7. Acid Treatment of pristine and sulfidized samples


#### 3.7.1 HCl treatment and kinetic modeling

Fe was steadily released from pristine GtNi6 and GtANi20 upon 3 M HCl treatment and Fe concentration in solution reached a plateau after ~24 hrs (Fig. 8a), even though the former dissolved slightly slower than the latter (inset in Fig. 8a). By contrast, Fe release from their sulfidized counterparts appeared more complex. The initial (~10 mins) Fe release from sulfidized samples is larger than that of their pristine equivalents (inset in Fig. 8a), likely as the result of Fe(II) desorption from mineral surfaces and from the dissolution of FeS<sub>x</sub> clusters and MIS. Following this initial fast stage, Fe release from sulfidized samples slowed down from 10 mins to ~12-24 hrs, a period during which goethite dissolution is the main process releasing Fe to solution. In contrast to pristine goethite samples that were thoroughly dissolved after 24 hrs of hydrochloric acid treatment, Fe release from sulfidized samples continued, most likely owing to dissolution of nanocrystalline pyrite at this stage, consistent with the enhanced solubility of fine-grained pyrite in HCl (Cornwell and Morse, 1987). Dissolution of fine-grained pyrite is supported by the overall Fe release during HCl treatment that exceeds the relative proportion of goethite and crystalline MIS determined by XRD in sulfidized samples (~60-67 wt% – Table S1, Fig. S6). These proportions do not account for FeS<sub>x</sub> clusters. Fe release rate was significantly decreased however, and no plateau was reached during the HCl treatment of sulfidized samples, even after 96 hrs.

The release of Ni associated to pristine goethite and to corresponding sulfidized samples differed significantly from that of Fe in these phases but also from one sample to the other (Fig. 8b). For example, Ni in GtNi6 was released slightly faster than Fe, both metals reaching a maximum concentration after ~24 hrs and complete goethite dissolution. In contrast, most adsorbed Ni present in GtANi20 was quickly released to the solution (~76% after 5 mins of the HCl acidic treatment) before reaching a plateau after ~7 hrs. Their sulfidized counterparts (GtNi6-44d and GtANi20-44d) exhibited contrasting Ni release rates before and after ~10 mins of interaction with HCl (inset in Fig. 8b), consistent with Fe release. In particular, ~25% and ~9% of Ni was released



from GtNi6-44d and GtANi20-44d, respectively, within the first 10 mins of interaction. After this initial fast release, which likely represents Ni associated to  $\text{FeS}_x$  clusters and MIS, Ni release from both samples appeared steady with no obvious rate modification.

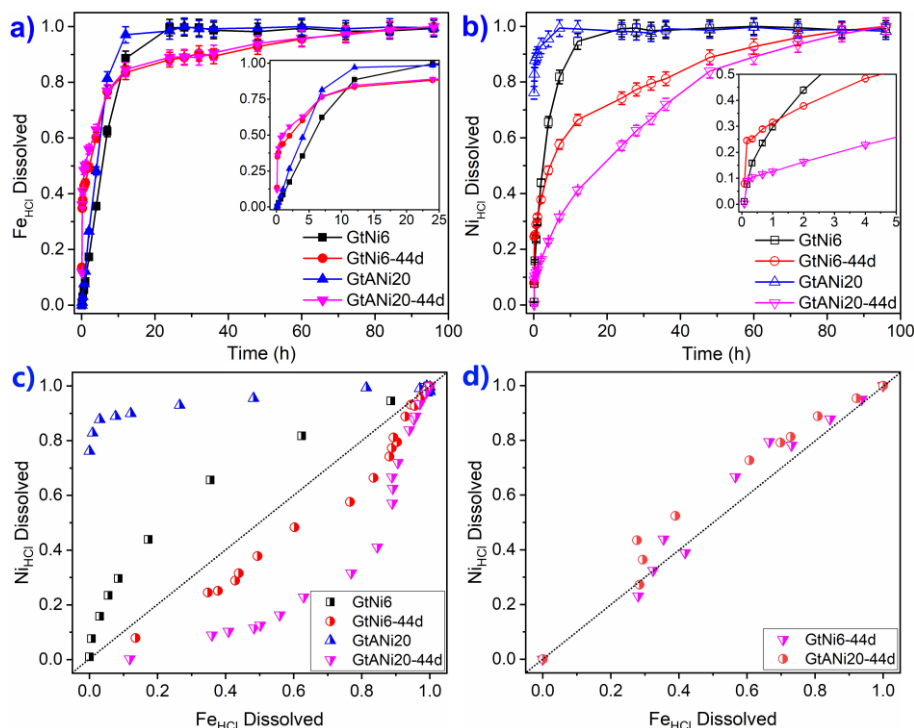


**Fig. 8.** Kinetic release of (a) Fe and (b) Ni during HCl treatment of pristine GtNi6 and GtANi20 and of their sulfidized counterparts. (c) Congruency of Ni versus Fe release during HCl treatment of pristine GtNi6 and GtANi20 and of their sulfidized counterparts during the whole treatment. (d) Congruency of Ni versus Fe release during HCl treatment of sulfidized samples (GtNi6-44d and GtANi20-44d) excluding data points before 24hrs. The  $y=x$  line is plotted as a dotted line in (c) and (d).

Simulations of Fe and Ni release kinetics during HCl treatment were performed using one-phase exponential decay function to evaluate the relative release of the two metals from pristine and sulfidized samples (Fig. S7, S8, and Table S3). The rates (1<sup>st</sup> derivative of kinetics) of Fe and Ni released from all the examined samples decreased as a function of time, and the relative release rate of Ni to Fe varied gradually (Fig. S7). For GtANi20, the adsorbed Ni experienced fast release while structural Fe was released gradually, producing an inverted-L relative release curve of Ni to Fe (Fig. 8c). For GtNi6, Ni (~69%) was released faster compared to Fe (~44%) before ~4.30 hrs and slower after that, yielding a convex relative release curve (Figs. 8c and S7), indicating

a non-uniform distribution of Ni in goethite (Girgin et al., 2011; Landers and Gilkes, 2007; Landers et al., 2009), with a significant Ni-enrichment in goethite outer layers. For sulfidized samples, Fe was released slightly or significantly faster relative to Ni upon the HCl treatment, and the rates dropped until equal to each other at ~9.60 hrs and ~7.10 hrs for GtNi6-44d and GtANi20-44d, respectively (Figs. 8c and S7). Although both sulfidized samples displayed rather similar trends of Fe release (~76% vs. ~78% after 7.70 hrs), Ni was released faster from GtNi6-44d than from GtANi20-44d before ~7.70 hrs (~60% vs. ~33%, Fig. S8). Interestingly, both sulfidized samples led to a concave relative release curve (Fig. 8c), that of GtNi6-44d being close to the  $y=x$  line. In contrast, that of GtANi20-44d was far from the line, indicating that Ni was more homogeneously distributed in GtNi6-44d compared to that in GtANi20-44d. In addition, GtANi20-44d most likely contained more Ni-free/poor phase(s) (residual goethite mainly) that were readily extracted by HCl and Ni-rich cores. The two sulfidized samples contained multiple Fe species [i.e., adsorbed Fe(II), goethite,  $\text{FeS}_x$  clusters, greigite, mackinawite, and pyrite], each likely releasing Fe at a different rate, especially during the first ~24 hrs of the treatment. To overcome this issue, the relative release curve was plotted excluding data points measured during this initial 24 hrs period (Fig. 8d). This curve was close to the  $y=x$  line, indicating Ni was homogeneously distributed in nanocrystalline pyrite.

### 3.7.2 $\text{HNO}_3$ treatment

When sulfidized samples pre-treated with HCl were equilibrated in 2 M  $\text{HNO}_3$ , the release of Fe and Ni proceeded (Fig. 9), accounting for the sole pyrite dissolution. For both GtNi6-44d and GtANi20-44d, Fe release rate was significantly enhanced by  $\text{HNO}_3$  treatment, and reached plateaus after ~48-72 hrs. Ni release was strongly correlated to that of Fe, leading to an almost linear relative release curve (Fig. 9c), indicative of a homogeneous Ni distribution in pyrite crystals.

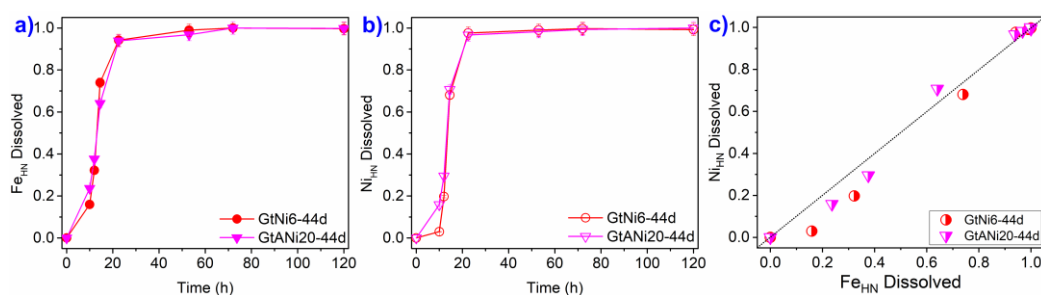

**Fig. 9.** Kinetic release of (a) Fe and (b) Ni during HNO<sub>3</sub> treatment of HCl-treated sulfidized GtNi6-44d and GtANi20-44d. (c) Congruency of Ni versus Fe release during HNO<sub>3</sub> treatment of HCl-treated sulfidized GtNi6-44d and GtANi20-44d. The y=x line is plotted as a dotted line in (c).

## 4. Discussion

### 4.1 Mineralogical evolution along goethite sulfidation

In the present study, diffraction (Figs. 1 and S1), electron microscopy (Figs. 5 and S5), and spectroscopic (Figs. 3, S2, and S3) data consistently show that crystalline products of goethite sulfidation consist mainly of pyrite with minor mackinawite and greigite. Sulfidation of goethite and other iron (oxyhydr)oxides thus appears as a pathway possibly accounting for the coexistence of iron (oxyhydr)oxides and of these iron sulfides in natural anoxic or alternating oxic-anoxic sediments and soils (Kalatha and Economou-Eliopoulos, 2015; Otero et al., 2009; Seyfferth et al., 2020). In nature, goethite and iron monosulfide (FeS) prevail in surface or subsurface horizons of soil profiles, whereas pyrite is the major iron-bearing mineral in deep horizons (Kraal et al., 2013; Seyfferth et al., 2020). Experimental studies, including the present one, provide additional insights into specific conditions favoring the formation of one phase or the other, common iron sulfides obtained from goethite sulfidation being amorphous FeS<sub>x</sub> clusters, mackinawite, greigite, and pyrite (Table 2). More especially, solution pH, relative abundance of goethite [(Fe(III))] and dissolved sulfides [S(-II)], and reaction duration appear to be responsible for reaction product diversity.

**Table 2**

Conditions of goethite reaction with S(-II) and mineralogy of iron sulfides reported in the literature and in the present study

c <sub>Fe</sub>	c <sub>S(-II)</sub>	Fe:S	pH	Reaction Duration	Products	Identification Methods	References
11.20	50.00	0.22	7.77	~2 hrs		XRD	Rickard, 1974
11.20	100.00	0.11	7.64				



11.20	200.00	0.06	7.50		amorphous		
11.20	400.00	0.03	7.24		FeS <sub>x</sub> ,		
11.20	500.00	0.02	6.95		mackinawite		
1.12	4.50	0.25	7.55				
5.10	4.16	1.23	7.61				
1.04	4.90	0.21	7.54	~24 hrs	iron	chemical	Pyzik and
3.17	2.60	1.22	7.54		monosulfide	method	Sommer,
1.06	5.50	0.19	7.42				1981
1.06	5.40	0.20	7.40				
n.i.	17.40		5.12	~2160 hrs	mackinawite,		Wang and
n.i.	17.60	**	5.06	~4320 hrs	greigite,	XRD, SEM	Morse,
n.i.	66.50		5.01	~4320 hrs	pyrite		1996
41.60	8.10	5.14	7.00	~168 hrs	mackinawite,	Mössbauer	Wan et al.,
3.40	14.90	0.23	7.00	~3672 hrs	pyrite	spectroscopy	2017
112.36	224.72	0.50	7.20	~336 hrs	mackinawite	XANES	Kumar et
112.36	112.36	1.00			mackinawite		al., 2018
11.20	11.20	1.00	6.00	~1056 hrs	mackinawite,	XRD, SEM,	This study
					greigite,	TEM	
					pyrite		

Note:  $c_{Fe}$  and  $c_{S(-II)}$  are given in mM. “n.i.” stands for “not indicated”, and \*\* indicates “S(-II) in excess”.

Mackinawite was identified in most studies listed in Table 2, and was consistently described as resulting from aging or crystallization of amorphous FeS<sub>x</sub> precursors, that would result from direct coprecipitation of Fe(II) and S(-II) according to Eq. 2 (Rickard, 1975; Schoonen and Barnes, 1991a). Both lower (< 7.0) pH conditions (Wang and Morse, 1996) and decreased Fe:S(-II) ratios (Kumar et al., 2018) increase dissolution rate of iron (oxyhydr)oxides and mackinawite precipitation rate. Although mackinawite readily precipitates in all runs of the present study, it hardly accumulates during sulfidation, compared to greigite and pyrite (Fig. 2 and Table S1). Two hypotheses may account for this specific behavior: i) the swift consumption of dissolved S(-II) (Fig. 6a) leads to low S(-II) levels, insufficient to precipitate mackinawite but allowing pyrite formation to proceed (Rickard and Luther, 2007); ii) mackinawite acts as a precursor for the formation of both greigite and pyrite (Wang and Morse, 1996). In addition, the initial formation of mackinawite provides active surfaces that favor pyrite nucleation and growth (Rickard and Luther, 2007), inhibiting further mackinawite formation and

growth. Mackinawite was also reported to be a necessary precursor for greigite formation (Rickard and Luther, 2007) through a rearrangement of Fe atoms in a [S(-II)] cubic close packing lattice and Fe loss to reach a proper Fe:S ratio (Lennie et al., 1997).

Formation of greigite along goethite sulfidation derived from XRD data analysis in the present work (Fig. 1) was consistently reported only by Wang and Morse (1996) in similar sulfidation experiments. In contrast, the presence of greigite was rejected in other studies from the analysis of Mössbauer spectra (Wan et al., 2017) or from the modeling of S K-edge XANES (X-ray absorption near edge structure) data (Kumar et al., 2018). These contrasting results suggest the key role of initial solution pH for greigite formation; sulfidation experiments of Wang and Morse (1996) were performed indeed under weakly acidic conditions consistent with the present ones (pH = 5.0 and 6.0, respectively), whereas those of Wan et al. (2017) and Kumar et al. (2018) were performed under circum-neutral conditions (pH = 7.0 or 7.2). Contrary to the present hypothesis derived from the comparison of experimental studies, Son et al. (2022) predicted from Density Functional Theory calculations that greigite stability and formation would be favored by higher pH conditions. These calculations were performed however for nanometer sized particles (~0.5-4 nm) to benefit from greigite lower surface energy compared to pyrite. In the present study, Rietveld refinement of XRD data indicates much larger crystal sizes (~15-18 nm along the 001 axis) for greigite. The Fe:S ratio appears less influential for greigite precipitation as Kumar et al. (2018) performed their experiments using a Fe:S ratio similar to that of the present study (Fe:S molar ratio  $\approx 1$ ).

Pyrite was formed in most goethite sulfidation experiments reported in the literature. Slightly alkaline conditions and low Fe:S(-II) ratios appear however to hamper pyrite formation (Kumar et al., 2018; Pyzik and Sommer, 1981; Rickard, 1974; Wan et al., 2017). Duration of the sulfidation experiment also appears as an important parameter for pyrite formation. Pyrite was not detected by Rickard (1974) and Pyzik and Sommer (1981) whose goethite sulfidation experiments lasted ~2 and ~24 hrs, respectively, whereas a minor amount of pyrite (~1-2%) was detected only after ~48 hrs by Wan et al. (2017) using Mössbauer spectroscopy, consistent with the present

study in which minor pyrite (~1-2 wt.%) was detected in sulfidation products after 3 days (Figs. 2, 3, and S1). In the present sulfidation experiments, pyrite formed massively from 3-7 days (Figs. 2, 3, S1, and S2). Low Fe:S(-II) ratios ( $\leq 0.2$ ) may delay further pyrite formation as shown by the presence of pyrite being detected only after ~56-60 days under such experimental conditions (Wan et al., 2017; Wang and Morse, 1996). Despite favorable Fe:S(-II) ratio (0.5-1.0) and sufficient duration (14 days), Kumar et al. (2018) discarded pyrite presence among goethite sulfidation products from the analysis of S K-edge XANES data. Contrasting initial solution pH values (7.2 vs. 6.0 in the present experiments) are most likely responsible for the much higher pyrite contents reported in the present experiments (~28.5-39.1% after 7-25 days – Fig. 2 and Table S1), consistent with the results of Wang and Morse (1996). Although pyrite is the dominant iron sulfide in most geological settings, Fe sulfidation or pyritization appears incomplete in many cases, with the persistence of MIS. Apart from the unfavorable conditions described above [low Fe:S(-II) ratio, slightly alkaline pH conditions], low concentration of  $S^0$  in solution (Fig. 6c) may also hamper MIS transformation to pyrite Wang and Morse (1996).

Consistently, colloidal FeS (or  $FeS_x$  clusters) were readily formed upon addition of goethite into the S(-II)-containing solutions, as the solution got black immediately after the addition (Hellige et al., 2012; Hockmann et al., 2020; Noël et al., 2020; Peiffer et al., 2015; Rickard, 1974), even after filtration through 0.22  $\mu m$  nylon filters (not shown). Solutions remained black-colored for about one week before turning colorless consistent with previous observations from ferrihydrite sulfidation (Noël et al., 2020). The timing of this color change roughly coincides with the remarkable decrease of  $S^0$  (Fig. 6c) and with the onset of the three crystalline iron sulfides identified by XRD in the present experiments (Fig. 2 and Table S1). This coincidence suggests that reaction between colloidal FeS (or  $FeS_x$  clusters) and  $S^0$  according to Eq. 2 most likely contributed to or even dominated the early formation of pyrite from goethite sulfidation (Hellige et al., 2012; Peiffer et al., 2015).

## 4.2 Influence of Ni on the sulfidation of goethite to pyrite

In this study, the influence of both adsorbed and structurally incorporated Ni on/in goethite on its sulfidation was assessed. The limited modification of Fe local environment in sulfidized Ni-bearing samples compared to Ni-free one (Figs. 3, S2, and S3) and the slower formation of pyrite (Fig. S1, Table S1) suggest that the presence of Ni hampered goethite sulfidation. Consistently, after 44 days of interaction with S(-II), reaction products of Ni-free goethite contain significantly more pyrite (54.4% vs. 33.2%, 33.5%, 33.0%, and 40.7%, Table S1) and less MIS (4.2% vs. 12.7%, 12.7%, 16.5%, and 11.7%, Table S1) than their counterparts from Ni-bearing goethites. A similar trend may be observed after 25 days of reaction (Fig. 2 and Table S1), suggesting that Ni stabilized MIS and delayed their complete conversion to pyrite, consistent with previous report (Swanner et al., 2019).

After the swift pyrite formation from 3-7 days in both Ni-free and -containing experiments, pyrite formation proceeded gradually (Fig. 2 and Table S1), indicating that MIS likely mediated this process at this later stage (Luther, 1991; Rickard and Luther, 2007), as colloidal FeS and FeS<sub>x</sub> clusters almost disappeared. During the pyritization process, destabilization of both FeS<sub>x</sub> clusters / colloidal FeS and MIS release Fe(II), likely contributing to the increase of [Fe(II)] in solution within the first ~15 days of reaction [Fig. 6b - (Butler and Rickard, 2000; Lennie et al., 1997)]. For all runs, the content of MIS was kept at a relatively low level (<2.7%) before 7 days, while after that MIS in Ni-containing groups accumulated up to 11.7%-16.6%. In contrast, MIS content in the Ni-free experiment only reached 4.2%, suggesting again that their association with Ni hindered the conversion of MIS to pyrite after 7 days.

The negative impact of Ni on MIS transformation to pyrite started earlier however. After 3 days of interaction with S(-II), iron sulfide formation is extremely marginal in all cases but modification of Fe local environment appears to be more limited in Ni-bearing goethites compared to Gt (Fig. S3). This reduced modification suggests also that the presence of Ni, both as adsorbed and incorporated species, decreases goethite reactivity towards S(-II). As proposed previously (Xu et al., 2006), the presence of Ni(II)

sorbed at the goethite surface possibly hinders subsequent sorption of other ions [S(-II) in this study]. In addition, the reduced surface charge resulting from Ni(II)-for-Fe(III) substitutions could also contribute to decrease goethite reactivity (de Carvalho-E-Silva et al., 2002). It should be noted however that in the present study similar kinetics of S(-II) consumption was measured for all reacting samples up to 3 days (Fig. 6a). This apparent inconsistency likely results from the fast decrease of S(-II) content originating from S(-II) adsorption to goethite surface, precipitation with Fe(II) and Ni(II), and formation of colloidal FeS and FeS<sub>x</sub> clusters, making adsorption specific contribution difficult to differentiate.

Mackinawite and FeS<sub>x</sub> cluster formation is considered to result from the direct coprecipitation of Fe(II) with S(-II) (Rickard and Luther, 2007), and dissolved Ni(II) precipitates more readily with S(-II) compared to Fe(II) [ $5.89 \times 10^{-10}$  vs.  $2.29 \times 10^{-4}$  for Ni and Fe, respectively – (Morse and Arakaki, 1993)]. The tendency of Ni to precipitate first as Ni-rich nuclei has been confirmed recently from TEM observations (Mansor et al., 2019), consistent with the present distribution of Ni in MIS particles (Figs. 7 and S5). In addition, mackinawite crystal growth rate increases in the presence of Ni(II), crystal structure being stabilized by Ni(II) (Ikogou et al., 2017). In the present work, mackinawite content remains limited in all experiments although the maximum mackinawite content [8.0(2) wt.%) was reported for GtANi20-44d (Table S1). The presence of Ni(II) appears to stabilize MIS as a whole (Fig. 2 and Table S1) however, possibly inhibiting their conversion to pyrite. The limited mackinawite content also suggests that the mackinawite-to-greigite transformation was not significantly hindered by Ni thus hampering the identification of a possible positive effect on mackinawite formation.

#### 4.3 The migration of Ni from goethite to iron sulfides

The systematic correlation between Ni and Fe sulfide polycrystals observed with electron microscopy (Figs. 7 and S5) evidenced the migration of Ni initially associated to goethite to iron sulfides (pyrite mainly) resulting from the sulfidation thereof. Acid treatments using HCl suggest however that Ni distribution within MIS depends on the

initial association mode of Ni with goethite. When initially incorporated in goethite structure, Ni is homogeneously distributed in newly formed sulfides whereas Ni appears to be enriched in MIS crystal cores when initially adsorbed onto goethite (Fig. 8c), consistent with previous reports (Mansor et al., 2019). In contrast, subsequent acid treatments using HNO<sub>3</sub> indicate that Ni was homogeneously distributed in newly formed pyrite, regardless of the initial association mode of Ni with goethite (Fig. 9c). It should be noted that Ni was not detected in solution during sulfidation of Ni-bearing goethite, implying that this process does not contribute Ni to sedimentary pore water in geological settings. In addition, the absence of dissolved Ni suggests that contrasting Ni distributions observed as a function of the initial association mode of Ni with goethite derive from differences in Ni and Fe release rates during the sulfidation of goethites. Specifically, adsorbed Ni(II) is most likely released faster compared to structural Fe, the latter being gradually released during goethite reductive dissolution. In addition, Ni(II) precipitates with S(-II) faster than Fe(II) (Morse and Arakaki, 1993) and thus concentrates mainly in the inner part of mackinawite particles. In contrast, Ni(II) structurally incorporated in GtNi<sub>6</sub> was released almost stoichiometrically with Fe(II), resulting in a homogeneous distribution of both metals within MIS crystals.

Although Ni(II) may be heterogeneously distributed within MIS crystals, its distribution within pyrite systematically appears to be homogeneous as suggested by the congruent release of Ni and Fe along the late (> 24 hrs) HCl and the whole HNO<sub>3</sub> acid treatments (Fig. 9c). This homogenous distribution in pyrite appears logical when MIS precursors also exhibit a homogeneous Ni distribution, owing to Fe(II) and Ni(II) interaction with S<sub>2</sub>(-II) onto mackinawite and greigite active surfaces to form pyrite (Rickard and Luther, 2007). In MIS formed from Ni-adsorbed goethite, Ni distribution is heterogeneous however, and redistribution of Ni between mackinawite and greigite most likely accounts for this apparent inconsistency. Specifically, mackinawite-to-greigite conversion is likely responsible for this redistribution before the subsequent formation of pyrite, as this conversion was described as the rearrangement of Fe (and Ni in the present study) atoms in a cubic close packing S(-II) lattice (Rickard and Luther, 2007). As a consequence and although a direct mackinawite-to-pyrite conversion was

proposed (Rickard, 1975), the formation of a greigite intermediate appears to be an efficient alternative pathway for pyrite formation from mackinawite, greigite occurrence increasing significantly pyrite formation rate (Lennie et al., 1997; Wang and Morse, 1996).

#### 4.4 Geochemical and environmental implications

In natural soil environments, Ni concentration usually increases with increasing depth (Michopoulos, 2021), goethite [and other iron (oxyhydr)oxides] and iron sulfides being common Fe-bearing minerals in upper and deeper horizons, respectively, both being Ni sinks (Ikogou et al., 2017; Morin et al., 2017; Swanner et al., 2019). Goethite is the main Ni host in oxide-type laterite deposits, which accounts for ~70% of Ni world's resources (Landers et al., 2009), the remaining ~30% being hosted in sulfide deposits. Although structural Ni incorporation usually prevails over surface complexation in both cases, Ni release to solution and/or transport to other phases can occur as the result of mineral dissolution or alteration under oxidative (Larsen and Postma, 1997; Nesbitt and Muir, 1994) or reductive (Landers and Gilkes, 2007; Landers et al., 2009) conditions. From the present results, Ni association to goethite slows down its possible conversion to Fe sulfides under reducing conditions, possibly accounting for goethite persistence in thermodynamically unfavorable S(-II)-rich conditions. Ni migration from Fe (oxyhydr)oxides to Fe sulfides along goethite sulfidation as reported in the present work most likely represents the main transport pathway for Ni from the oxic zone to the anoxic zone however. In turn, the swift release of Ni to solution upon the oxidative alteration of Ni-bearing Fe sulfides, in acid mine drainage for example, is a key process of Ni geochemical cycling.

#### Conclusions

The mineralogical evolution observed in the present study along goethite sulfidation is consistent with the commonly accepted reaction mechanisms for this process. The mineralogical sequence, and thus mechanisms at play, is similar for both Ni-free and Ni-containing goethites and involves the swift initial formation of colloidal



FeS, FeS<sub>x</sub> clusters, and metastable iron sulfides (mackinawite and greigite) prior to pyrite formation that is detected after ~3 days of interaction with S(-II). The early (~3-7 days) formation of pyrite originates from the reaction between colloidal FeS, FeS<sub>x</sub> clusters, and S<sup>0</sup>, and the later stage (~7-44 days) mainly comes from the conversion of metastable iron sulfides. Consistent with previous reports, greigite formation appears to be favored by slightly acidic pH conditions (pH = 6.0). These conditions also enhance pyrite crystallization, whereas low Fe:S(-II) ratios ( $\leq 0.2$ ) negatively impact pyrite formation. Compared to the Ni-free system, pyrite formation rate is also decreased by the presence of Ni, independent of its association mode with goethite, i.e., adsorption or isomorphic substitution. Ni appears indeed to reduce the reactivity of goethite to S(-II) and increase MIS stability, the overall sulfidation progress, as measured by Fe local environment and the relative proportion of sulfides and goethite, being similar in all cases. Incorporation of Ni in intermediate MIS also buffers its subsequent release and induces a uniform distribution of this element in newly formed pyrite, independent of its initial association mode with goethite.

## Acknowledgements

This work is supported by the National Natural Science Foundations of China (No. 42107319, 42225704, and 42077290). We are grateful to Dr. Zhongjun Chen and Dr. Yunpeng Liu at BSRF for their assistance with Fe K-edge XAFS data collection and analysis, and we thank Dr. Jiang Xu at Zhejiang University for providing XAFS standards of pyrite and mackinawite, and Dr. Shuang Zhang at Huazhong Agricultural University is appreciated for her help with XRD data collection. Dr. Vincent Noël kindly provided the EXAFS reference spectrum of colloidal FeS. ISTerre is part of Labex OSUG@2020 (ANR10-LABX56).

## Research Data

Research Data related to this article includes: Chemical compositions; XRD data; XAS data at Fe K-edges; TGA data; Solution chemistry; Fe/Ni release upon HCl/HNO<sub>3</sub> treatment. Dataset can be accessed at Mendeley Data, V1, doi: 10.17632/khhhyhkhkz.1.



## Appendix A. Supplementary Material

Supplementary material includes i) XRD patterns showing the mineralogical evolution of goethite samples as a function of sulfidation duration and results of Rietveld refinements performed on this data (quantitative phase analysis and unit-cell parameters of the main minerals present), ii) Fe K-edge EXAFS spectra of pritsine and sulfidized goethite samples and difference thereof, iii) TEM micrographs, SAED, and STEM-HAADF data obtained on sulfidized samples, and iv) modeling of Fe and Ni kinetic release upon HCl treatment of goethite samples.

## References

- Bagarinao T. (1992) Sulfide as an environmental factor and toxicant: tolerance and adaptations in aquatic organisms. *Aquat. Toxicol.* **24**, 21-62.
- Biber M. V., dos Santos Afonso M. and Stumm W. (1994) The coordination chemistry of weathering: IV. Inhibition of the dissolution of oxide minerals. *Geochim. Cosmochim. Acta* **58**, 1999-2010.
- Bishop D. W., Thomas P. S. and Ray A. S. (1999)  $\alpha$ - $\beta$  Phase Re-Transformation Kinetics in Nickel Sulphide. *J. Therm. Anal. Calorim.* **56**, 429-435.
- Burton E. D., Johnston S. G., Watling K., Bush R. T., Keene A. F. and Sullivan L. A. (2010) Arsenic Effects and Behavior in Association with the Fe(II)-Catalyzed Transformation of Schwertmannite. *Environ. Sci. Technol.* **44**, 2016-2021.
- Butler I. B. and Rickard D. (2000) Framboidal pyrite formation via the oxidation of iron (II) monosulfide by hydrogen sulphide. *Geochim. Cosmochim. Acta* **64**, 2665-2672.
- Canfield D. E. (1989) Reactive iron in marine sediments. *Geochim. Cosmochim. Acta* **53**, 619-632.
- Canfield D. E., Raiswell R. and Bottrell S. H. (1992) The reactivity of sedimentary iron minerals toward sulfide. *Am. J. Sci.* **292**, 659-683.
- Cao F., Hu W., Zhou L., Shi W., Song S., Lei Y., Wang S. and Zhang H. (2009) 3D Fe<sub>3</sub>S<sub>4</sub> flower-like microspheres: high-yield synthesis via a biomolecule-assisted solution approach, their electrical, magnetic and electrochemical hydrogen storage properties. *Dalton Trans.* 10.1039/b912569h, 9246-9252.
- Cline J. D. (1969) Spectrophotometric determination of hydrogen sulfide in natural waters. *Limnol. Oceanogr.* **14**, 454-458.
- Cooper D. C. and Morse J. W. (1998) Extractability of Metal Sulfide Minerals in Acidic Solutions: Application to Environmental Studies of Trace Metal Contamination

816 within Anoxic Sediments. *Environ. Sci. Technol.* **32**, 1076-1078.

817 Cornell R. M. (1991) Simultaneous incorporation of Mn, Ni and Co in the goethite  
818 ( $\alpha$ -FeOOH) structure. *Clay Miner.* **26**, 427-430.

819 Cornell R. M. and Schwertmann U. (2004) *The Iron Oxides: Structure, Properties,*  
820 *Reactions, Occurrences and Uses, Second Edition.*

821 Cornwell J. C. and Morse J. W. (1987) The characterization of iron sulfide minerals in  
822 anoxic marine sediments. *Mar. Chem.* **22**, 193-206.

823 de Carvalho-E-Silva M. L. M., Partiti C. S. M., Enzweiler J., Petit S., Netto S. M. and  
824 de Oliveira S. M. B. (2002) Characterization of Ni-containing goethites by  
825 Mossbauer spectroscopy and other techniques. *Hyperfine Interact.* **142**, 559-576.

826 Deoliveira S. M. B., Trescases J. J. and Melfi A. J. (1992) Lateritic Nickel deposits of  
827 Brazil. *Miner. Deposita* **27**, 137-146.

828 Döbelin N. (2015) Interlaboratory study on the quantification of calcium phosphate  
829 phases by Rietveld refinement. *Powder Diffr.* **30**, 231-241.

830 Döbelin N. and Kleeberg R. (2015) Profex: a graphical user interface for the Rietveld  
831 refinement program BGMN. *J. Appl. Crystallogr.* **48**, 1573-1580.

832 Dos Santos Afonso M. and Stumm W. (1992) Reductive dissolution of iron(III)  
833 (hydr)oxides by hydrogen sulfide. *Langmuir* **8**, 1671-1675.

834 Du R., Xian H., Wu X., Zhu J., Wei J., Xing J., Tan W. and He H. (2021) Morphology  
835 dominated rapid oxidation of framboidal pyrite. *Geochem. Perspect. Let.* **16**,  
836 53-58.

837 Dubbin W. E. and Bullough F. (2017) Dissolution of Al-Substituted Goethite in the  
838 Presence of Ferrichrome and Enterobactin at pH 6.5. *Aquat. Geochem.* **23**, 61-  
839 74.

840 Dublet G., Juillot F., Morin G., Fritsch E., Fandeur D. and Brown Jr G. E. (2015)  
841 Goethite aging explains Ni depletion in upper units of ultramafic lateritic ores  
842 from New Caledonia. *Geochim. Cosmochim. Acta* **160**, 1-15 %@ 0016-7037.

843 Dublet G., Juillot F., Morin G., Fritsch E., Fandeur D., Ona-Nguema G. and Brown Jr  
844 G. E. (2012) Ni speciation in a New Caledonian lateritic regolith: a quantitative  
845 X-ray absorption spectroscopy investigation. *Geochim. Cosmochim. Acta* **95**,  
846 119-133.

847 Dunn J. G. and Kelly C. E. (1977) A TG/DTA/MS study of the oxidation of nickel  
848 sulphide. *J. Therm. Anal.* **12**, 43-52.

849 Elias M. (2002) Nickel laterite deposits – geological overview, resources and  
850 exploitation.

851 Eliopoulos D. G. and Economou-Eliopoulos M. (2000) Geochemical and mineralogical  
852 characteristics of Fe–Ni- and bauxitic-laterite deposits of Greece. *Ore Geol. Rev.*  
853 **16**, 41-58.

854 Fadrus H. and Malý J. (1975) Suppression of iron(III) interference in the determination  
855 of iron(II) in water by the 1,10-phenanthroline method. *Analyst* **100**, 549-554.

856 Fan R. and Gerson A. R. (2015) Synchrotron micro-spectroscopic examination of  
857 Indonesian nickel laterites. *Am. Mineral.* **100**, 926-934.

858 Frierdich A. J., McBride A., Tomkinson S. and Southall S. C. (2019) Nickel Cycling  
859 and Negative Feedback on Fe(II)-Catalyzed Recrystallization of Goethite. *ACS*

860 *Earth Space Chem.* **3**, 1932-1941.

861 Gasser U. G., Jeanroy E., Mustin C., Barres O., Nuesch R., Berthelin J. and Herbillon  
862 A. J. (1996) Properties of synthetic goethites with Co for Fe substitution. *Clay*  
863 *Miner.* **31**, 465-476.

864 Girgin I., Obut A. and Ucyildiz A. (2011) Dissolution behaviour of a Turkish lateritic  
865 nickel ore. *Miner. Eng.* **24**, 603-609.

866 Hellige K., Pollok K., Larese-Casanova P., Behrends T. and Peiffer S. (2012) Pathways  
867 of ferrous iron mineral formation upon sulfidation of lepidocrocite surfaces.  
868 *Geochim. Cosmochim. Acta* **81**, 69-81.

869 Hockmann K., Planer-Friedrich B., Johnston S. G., Peiffer S. and Burton E. D. (2020)  
870 Antimony mobility in sulfidic systems: Coupling with sulfide-induced iron  
871 oxide transformations. *Geochim. Cosmochim. Acta* **282**, 276-296.

872 Hohmann C., Morin G., Ona-Nguema G., Guigner J. M., Brown G. E. and Kappler A.  
873 (2011) Molecular-level modes of As binding to Fe(III) (oxyhydr)oxides  
874 precipitated by the anaerobic nitrate-reducing Fe(II)-oxidizing *Acidovorax* sp  
875 strain BoFeN1. *Geochim. Cosmochim. Acta* **75**, 4699-4712.

876 Huang F.-G., Jia S.-Y., Liu Y., Wu S.-H. and Han X. (2015) Reductive dissolution of  
877 ferrihydrite with the release of As(V) in the presence of dissolved S(-II). *J.*  
878 *Hazard. Mater.* **286**, 291-297.

879 Huerta-Diaz M. A. and Morse J. W. (1990) A quantitative method for determination of  
880 trace metal concentrations in sedimentary pyrite. *Mar. Chem.* **29**, 119-144.

881 Hurtgen M. T., Lyons T. W., Ingall E. D. and Cruse A. M. (1999) Anomalous  
882 enrichments of iron monosulfide in euxinic marine sediments and the role of  
883 H<sub>2</sub>S in iron sulfide transformations: Examples from Effingham Inlet, Orca  
884 Basin, and the Black Sea. *Am. J. Sci.* **299**, 556-588.

885 Ikogou M., Ona-Nguema G., Juillot F., Le Pape P., Menguy N., Richeux N., Guigner J.  
886 M., Noel V., Brest J., Baptiste B. and Morin G. (2017) Long-term sequestration  
887 of nickel in mackinawite formed by *Desulfovibrio capillatus* upon Fe(III)-citrate  
888 reduction in the presence of thiosulfate. *Appl. Geochem.* **80**, 143-154.

889 Islam M. and Patel R. (2017) Solvothermal synthesis of greigite (Fe<sub>3</sub>S<sub>4</sub>)- Conducting  
890 polypyrrole nanocomposite and its application towards arsenic removal. *Sep.*  
891 *Sci. Technol.* **52**, 2835-2852.

892 Kalatha S. and Economou-Eliopoulos M. (2015) Framboidal pyrite and bacterio-  
893 morphic goethite at transitional zones between Fe-Ni-laterites and limestones:  
894 Evidence from Lokris, Greece. *Ore Geol. Rev.* **65**, 413-425.

895 Kraal P., Burton E. D. and Bush R. T. (2013) Iron monosulfide accumulation and pyrite  
896 formation in eutrophic estuarine sediments. *Geochim. Cosmochim. Acta* **122**,  
897 75-88.

898 Krs M., Novak F., Krsova M., Pruner P. and Jansa J. (1993) Magnetic-properties, self-  
899 reversal remanence and thermal alteration products of smythite *Stud. Geophys.*  
900 *Geod.* **37**, 382-400.

901 Kumar N., Pacheco J. L., Noel V., Dublet G. and Brown G. E. (2018) Sulfidation  
902 mechanisms of Fe(III)-(oxyhydr)oxide nanoparticles: a spectroscopic study.  
903 *Environ. Sci. Nano* **5**, 1012-1026.

904 Kyprianidou-Leodidou T., Althaus H. J., Wyser Y., Vetter D., Buchler M., Caseri W. and  
905 Suter U. W. (1997) High refractive index materials of iron sulfides and  
906 poly(ethylene oxide). *J. Mater. Res.* **12**, 2198-2206.

907 Lan Y. and Butler E. C. (2014) Monitoring the transformation of mackinawite to greigite  
908 and pyrite on polymer supports. *Appl. Geochem.* **50**, 1-6.

909 Landers M. and Gilkes R. J. (2007) Dehydroxylation and dissolution of nickeliferous  
910 goethite in New Caledonian lateritic Ni ore. *Appl. Clay Sci.* **35**, 162-172.

911 Landers M., Gilkes R. J. and Wells M. (2009) Dissolution kinetics of dehydroxylated  
912 nickeliferous goethite from limonitic lateritic nickel ore. *Appl. Clay Sci.* **42**,  
913 615-624.

914 Larsen F. and Postma D. (1997) Nickel mobilization in a groundwater well field: release  
915 by pyrite oxidation and desorption from manganese oxides. *Environ. Sci.*  
916 *Technol.* **31**, 2589-2595.

917 Larsen O. and Postma D. (2001) Kinetics of reductive bulk dissolution of lepidocrocite,  
918 ferrihydrite, and goethite. *Geochim. Cosmochim. Acta* **65**, 1367-1379.

919 Lennie A. R., Redfern S. A. T., Champness P. E., Stoddart C. P., Schofield P. F. and  
920 Vaughan D. J. (1997) Transformation of mackinawite to greigite: An in situ X-  
921 ray powder diffraction and transmission electron microscope study. *Am.*  
922 *Mineral.* **82**, 302-309.

923 Liu J., Pellerin A., Wang J., Rickard D., Antler G., Zhao J., Wang Z., Jørgensen B. B.  
924 and Ono S. (2022) Multiple sulfur isotopes discriminate organoclastic and  
925 methane-based sulfate reduction by sub-seafloor pyrite formation. *Geochim.*  
926 *Cosmochim. Acta* **316**, 309-330.

927 Lowers H. A., Breit G. N., Foster A. L., Whitney J., Yount J., Uddin N. and Muneem A.  
928 (2007) Arsenic incorporation into authigenic pyrite, bengal basin sediment,  
929 Bangladesh. *Geochim. Cosmochim. Acta* **71**, 2699-2717.

930 Luther G. W. (1991) Pyrite synthesis via polysulfide compounds. *Geochim. Cosmochim.*  
931 *Acta* **55**, 2839-2849.

932 Manceau A., Schlegel M. L., Musso M., Sole V. A., Gauthier C., Petit P. E. and Trolard  
933 F. (2000) Crystal chemistry of trace elements in natural and synthetic goethite.  
934 *Geochim. Cosmochim. Acta* **64**, 3643-3661.

935 Mansor M., Winkler C., Hochella M. F., Jr. and Xu J. (2019) Nanoparticulate Nickel-  
936 Hosting Phases in Sulfidic Environments: Effects of Ferrous Iron and Bacterial  
937 Presence on Mineral Formation Mechanism and Solid-Phase Nickel  
938 Distribution. *Front. Earth Sci.* **7**.

939 Maurice P. A., Lee Y. J. and Hersman L. E. (2000) Dissolution of Al-substituted  
940 goethites by an aerobic *Pseudomonas mendocina* var. bacteria. *Geochim.*  
941 *Cosmochim. Acta* **64**, 1363-1374.

942 Michopoulos P. (2021) Nickel in forests - a short review on its distribution and fluxes.  
943 *Folia Oecologica* **48**, 205-214.

944 Morin G., Noel V., Menguy N., Brest J., Baptiste B., Tharaud M., Ona-Nguema G.,  
945 Ikogou M., Viollier E. and Juillot F. (2017) Nickel accelerates pyrite nucleation  
946 at ambient temperature. *Geochem. Perspect. Lett.* **5**, 6-11.

947 Morse J. W. and Arakaki T. (1993) Adsorption and coprecipitation of divalent metals

948 with mackinawite (FeS). *Geochim. Cosmochim. Acta* **57**, 3635-3640.

949 Morse J. W. and Luther G. W. (1999) Chemical influences on trace metal-sulfide  
950 interactions in anoxic sediments. *Geochim. Cosmochim. Acta* **63**, 3373-3378.

951 Morse J. W., Millero F. J., Cornwell J. C. and Rickard D. (1987) The chemistry of the  
952 hydrogen sulfide and iron sulfide systems in natural waters. *Earth Sci. Rev.* **24**,  
953 1-42.

954 Nachtegaal M. and Spark D. L. (2002) Kinetics and mechanisms of nickel surface  
955 precipitation in multi-sorbent system: a spectroscopic study. *In: 17th WCSS,*  
956 *Thailand*, 1345-1355.

957 Nesbitt H. W. and Muir I. J. (1994) X-ray photoelectron spectroscopic study of a pristine  
958 pyrite surface reacted with water-vapor and air. *Geochim. Cosmochim. Acta* **58**,  
959 4667-4679.

960 Noël V., Kumar N., Boye K., Barragan L., Lezama-Pacheco J. S., Chu R., Tolic N.,  
961 Brown G. E. and Bargar J. R. (2020) FeS colloids - formation and mobilization  
962 pathways in natural waters. *Environ. Sci. Nano* **7**, 2102-2116.

963 Noël V., Morin G., Juillot F., Marchand C., Brest J., Bargar J. R., Munoz M., Marakovic  
964 G., Ardo S. and Brown G. E., Jr. (2015) Ni cycling in mangrove sediments from  
965 New Caledonia. *Geochim. Cosmochim. Acta* **169**, 82-98.

966 Otero X. L., Ferreira T. O., Huerta-Diaz M. A., Partiti C. S. M., Souza V., Vidal-Torrado  
967 P. and Macias F. (2009) Geochemistry of iron and manganese in soils and  
968 sediments of a mangrove system, Island of Pai Matos (Cananeia - SP, Brazil).  
969 *Geoderma* **148**, 318-335.

970 Peiffer S., Behrends T., Hellige K., Larese-Casanova P., Wan M. and Pollok K. (2015)  
971 Pyrite formation and mineral transformation pathways upon sulfidation of ferric  
972 hydroxides depend on mineral type and sulfide concentration. *Chem. Geol.* **400**,  
973 44-55.

974 Ponomar V. P. (2018) Thermomagnetic properties of the goethite transformation during  
975 high-temperature treatment. *Miner. Eng.* **127**, 143-152.

976 Poulton S. W. (2003) Sulfide oxidation and iron dissolution kinetics during the reaction  
977 of dissolved sulfide with ferrihydrite. *Chem. Geol.* **202**, 79-94.

978 Poulton S. W., Krom M. D. and Raiswell R. (2004) A revised scheme for the reactivity  
979 of iron (oxyhydr)oxide minerals towards dissolved sulfide. *Geochim.*  
980 *Cosmochim. Acta* **68**, 3703-3715.

981 Pyzik A. J. and Sommer S. E. (1981) Sedimentary iron monosulfides: Kinetics and  
982 mechanism of formation. *Geochim. Cosmochim. Acta* **45**, 687-698.

983 Ravel B. and Newville M. (2005) ATHENA and ARTEMIS: interactive graphical data  
984 analysis using IFEFFIT. *Phys. Scr.* **2005**, 1007.

985 Ren H.-T., Ji Z.-Y., Wu S.-H., Han X., Liu Z.-M. and Jia S.-Y. (2018) Photoreductive  
986 dissolution of schwertmannite induced by oxalate and the mobilization of  
987 adsorbed As(V). *Chemosphere* **208**, 294-302.

988 Rickard D. (1975) Kinetics and mechanism of pyrite formation at low temperatures.  
989 *Am. J. Sci.* **275**, 636-652.

990 Rickard D. and Luther G. W. (2007) Chemistry of Iron Sulfides. *Chem. Rev.* **107**, 514-  
991 562.

- Rickard D. T. (1974) Kinetics and mechanism of the sulfidation of goethite. *Am. J. Sci.* **274**, 941-952.
- Sagnotti L. and Winkler A. (1999) Rock magnetism and palaeomagnetism of greigite-bearing mudstones in the Italian peninsula. *Earth Planet. Sci. Lett.* **165**, 67-80.
- Schoonen M. A. A. and Barnes H. L. (1991a) Reactions forming pyrite and marcasite from solution: II. Via FeS precursors below 100 °C. *Geochim. Cosmochim. Acta* **55**, 1505-1514.
- Schoonen M. A. A. and Barnes H. L. (1991b) Reactions forming pyrite and marcasite from solution: I. Nucleation of FeS<sub>2</sub> below 100°C. *Geochim. Cosmochim. Acta* **55**, 1495-1504.
- Seyfferth A. L., Bothfeld F., Vargas R., Stuckey J. W., Wang J., Kearns K., Michael H. A., Guimond J., Yu X. and Sparks D. L. (2020) Spatial and temporal heterogeneity of geochemical controls on carbon cycling in a tidal salt marsh. *Geochim. Cosmochim. Acta* **282**, 1-18.
- Son S., Hyun S. P., Charlet L. and Kwon K. D. (2022) Thermodynamic stability reversal of iron sulfides at the nanoscale: Insights into the iron sulfide formation in low-temperature aqueous solution. *Geochim. Cosmochim. Acta* **338**, 220-228.
- Suter D., Banwart S. and Stumm W. (1991) Dissolution of hydrous Iron(III) oxides by reductive mechanisms. *Langmuir* **7**, 809-813.
- Swanner E. D., Webb S. M. and Kappler A. (2019) Fate of cobalt and nickel in mackinawite during diagenetic pyrite formation. *Am. Mineral.* **104**, 917-928.
- Ugwu I. M. and Sherman D. M. (2019) The solubility of goethite with structurally incorporated nickel and cobalt: Implication for laterites. *Chem. Geol.* **518**, 1-8.
- Ugwu I. M., Sherman D. M. and Bacon C. G. D. (2019) Sorption of nickel onto goethite (alpha-FeOOH) and desorption kinetics of aged synthetic Ni-goethite: Implication for Ni laterite ore. *Chem. Geol.* **509**, 223-233.
- Wan M., Schroeder C. and Peiffer S. (2017) Fe(III): S(-II) concentration ratio controls the pathway and the kinetics of pyrite formation during sulfidation of ferric hydroxides. *Geochim. Cosmochim. Acta* **217**, 334-348.
- Wang Q. W. and Morse J. W. (1996) Pyrite formation under conditions approximating those in anoxic sediments .1. Pathway and morphology. *Mar. Chem.* **52**, 99-121.
- Wells M. A., Fitzpatrick R. W. and Gilkes R. J. (2006) Thermal and mineral properties of Al-, Cr-, Mn-, Ni- and Ti-substituted goethite. *Clays Clay Miner.* **54**, 176-194.
- Xu Y., Axe L., Yee N. and Dyer J. A. (2006) Bidentate complexation modeling of heavy metal adsorption and competition on goethite. *Environ. Sci. Technol.* **40**, 2213-2218.
- Yang F., Lai Y. and Song Y. (2019) Determination of the influence of pyrite on coal spontaneous combustion by thermodynamics analysis. *Process Saf. Environ. Prot.* **129**, 163-167.
- Zachara J. M., Fredrickson J. K., Smith S. C. and Gassman P. L. (2001) Solubilization of Fe(III) oxide-bound trace metals by a dissimilatory Fe(III) reducing bacterium. *Geochim. Cosmochim. Acta* **65**, 75-93.

## Supplementary Material to:

### Sulfidation of Ni-bearing goethites to pyrite: the effects of Ni and implications for its migration between iron phases

Zhongkuan Wu<sup>a</sup>, Tingting Zhang<sup>a</sup>, Bruno Lanson<sup>b</sup>, Hui Yin<sup>c</sup>, Dong  
Cheng<sup>a</sup>, Peng Liu<sup>d</sup>, Feng He<sup>a,e,\*</sup>

<sup>a</sup>*College of Environment, Zhejiang University of Technology, Hangzhou 310014,  
China*

<sup>b</sup>*Univ. Grenoble Alpes, Univ. Savoie Mont Blanc, CNRS, IRD, Univ. Gustave Eiffel,  
ISTerre, F-38000 Grenoble, France*

<sup>c</sup>*Key Laboratory of Arable Land Conservation (Middle and Lower Reaches of Yangtse  
River), Ministry of Agriculture and Rural Affairs, College of Resources and  
Environment, Huazhong Agricultural University, Wuhan 430070, China*

<sup>d</sup>*School of Environmental Studies & State Key Laboratory of Biogeology and  
Environmental Geology, China University of Geosciences, Wuhan 430074, China*

<sup>e</sup>*Environment and Civil Engineering, Jiangnan University, Wuxi, Jiangsu, 214122,  
China*

Corresponding author.

E-mail address: [fenghe@zjut.edu.cn](mailto:fenghe@zjut.edu.cn) (Feng He).

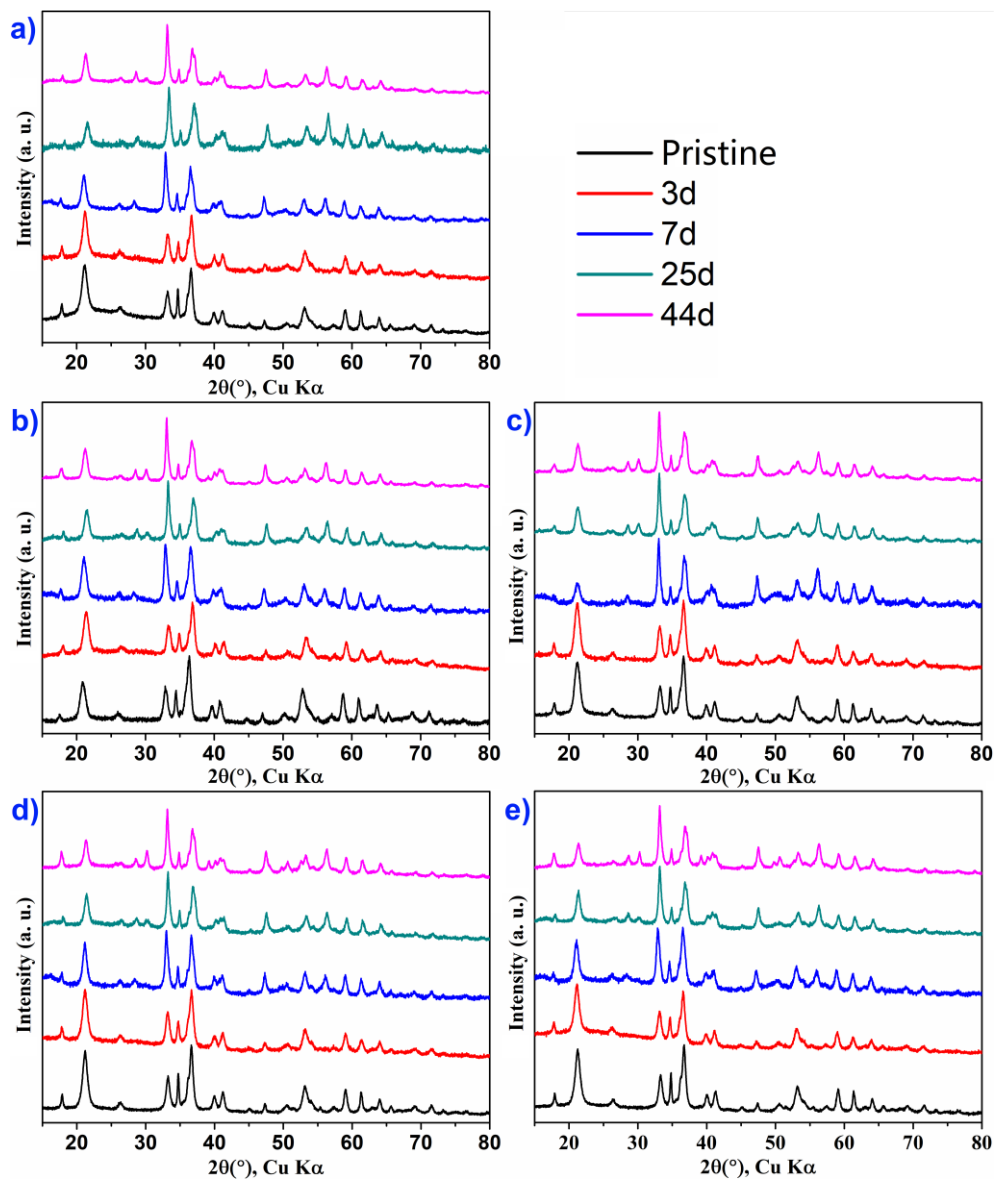


Fig. S1. Evolution of XRD patterns of Ni-free/-containing goethites as a function of sulfidation duration: a): Gt, b): GtNi2, c): GtNi6, d): GtANi5, and e): GtANi20.



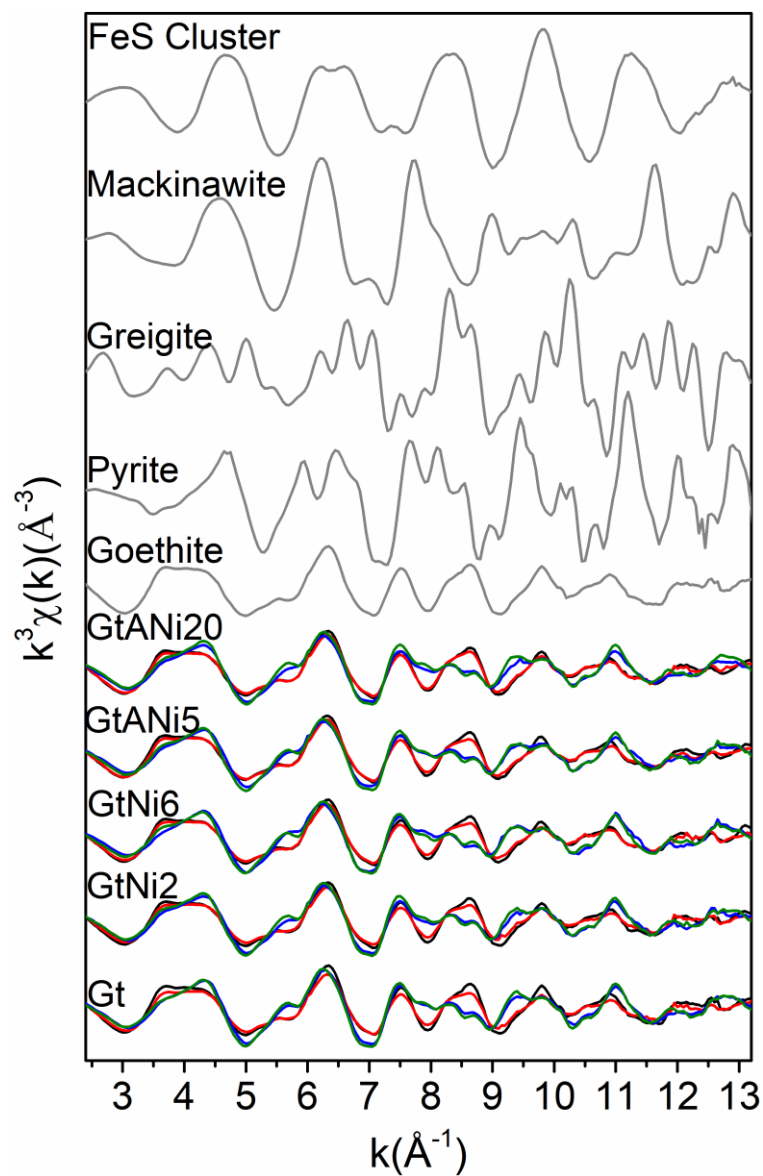


Fig. S2. Fe K-edge EXAFS spectra ( $k^3$  weighted) obtained for pristine (black) and sulfidized goethite samples (red: 3 days, blue: 7 days, olive green: 44 days), and iron oxyhydroxide/sulfide standards (gray). Data for colloidal FeS from [Noël et al. \(2020\)](#). The Fe K-edge EXAFS spectrum of greigite was calculated with Feff8.4 ([Ikogou et al., 2017](#)) based on its structure model (COD#9000123).

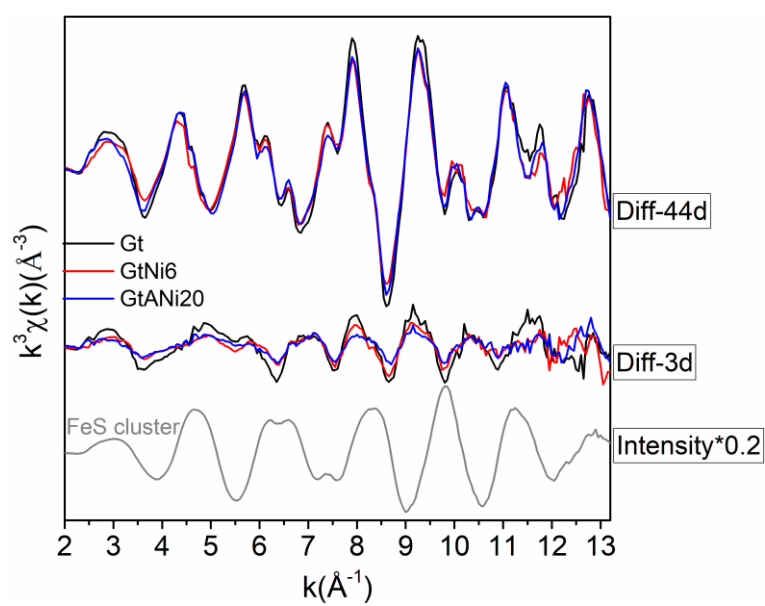


Fig. S3. Difference of Fe K-edge EXAFS spectra ( $k^3$  weighted) between pristine and sulfidized samples (3 or 44 days of sulfidation) by comparison with a FeS cluster standard.

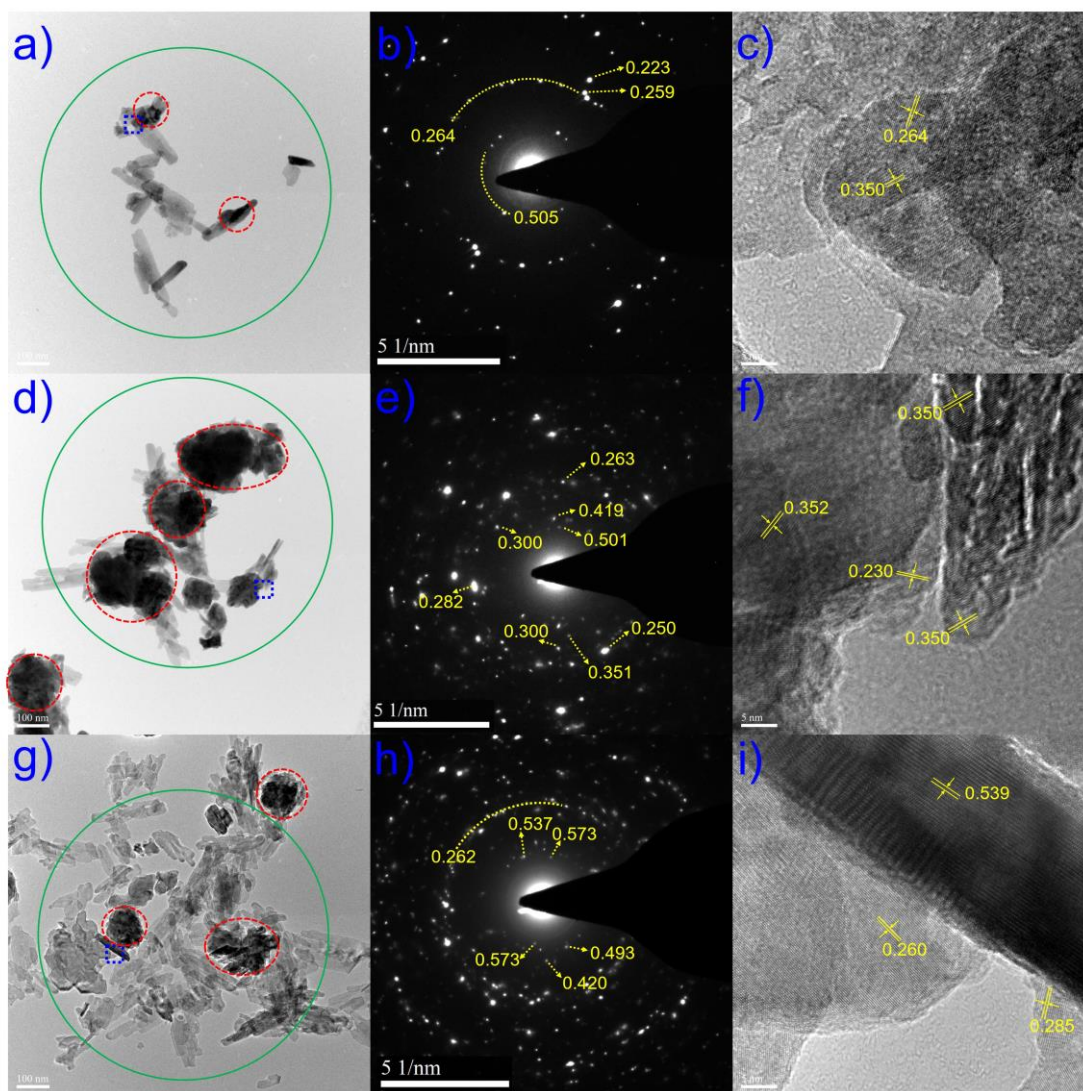


Fig. S4. Low magnification TEM images (scale bar is 100 nm) of samples sulfidized for 44 days: a): Gt-44d, d): GtNi6-44d, and g): GtANi20-44d. Those fibrous morphologies represent residual goethite crystals, and red dotted circles outlining polycrystalline aggregates indicate iron sulfides. b), e), and h): selected area electron diffraction (SAED) patterns of green circles indicated areas in a), d), and g), respectively. c), f), and i): high magnification images (scale bar is 5 nm) of the blue dotted rectangles shown in a), d), and g), respectively. Yellow values plotted on SAED patterns and lattice fringe images are distances (in nm). In particular,  $\sim 0.282/0.285$ ,  $\sim 0.350$ , and  $0.573$  nm correspond to (222), (220), and (111) of greigite (ICDD#16-0713) respectively, and that of  $\sim 0.537/0.539$  nm are ascribed to (100) of pyrite (ICDD#42-1340), and  $\sim 0.300$  nm indicates (311) of greigite or (101) of mackinawite (ICDD#15-0037). These numbers above couldn't be attributed to any plane of goethite (ICDD#29-0713).

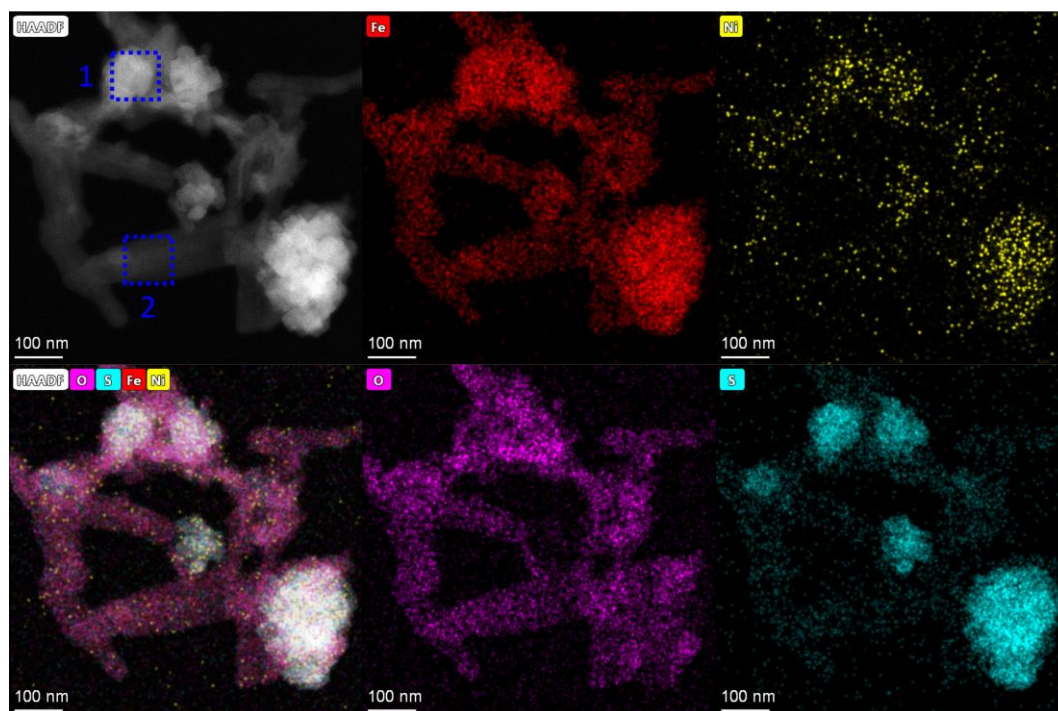


Fig. S5. STEM/HAADF micrograph (upper left) and EDX maps for Fe (upper center), Ni (upper right), O (lower center), S (lower right), and composite Fe-Ni-S-O obtained for GtNi6-44d. Ni mass fraction in area #1 (HAADF image) was  $0.98 \pm 0.21\%$ , that in area #2 was  $0.82 \pm 0.50\%$ .

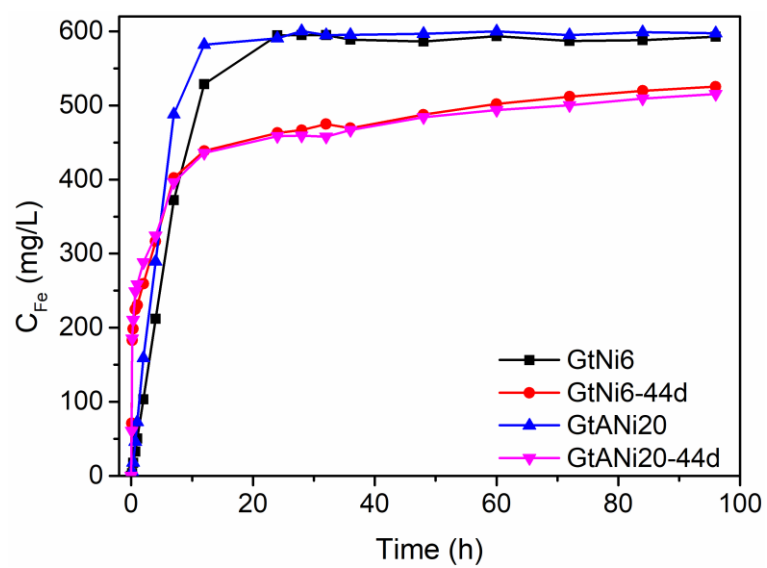


Fig. S6. Kinetic release of Fe (in concentration) during HCl treatment of pristine GtNi6 and GtANi20 and of their sulfidized counterparts. After 24 hrs, ~75% of Fe initially present in pristine goethites has been released from sulfidized samples.

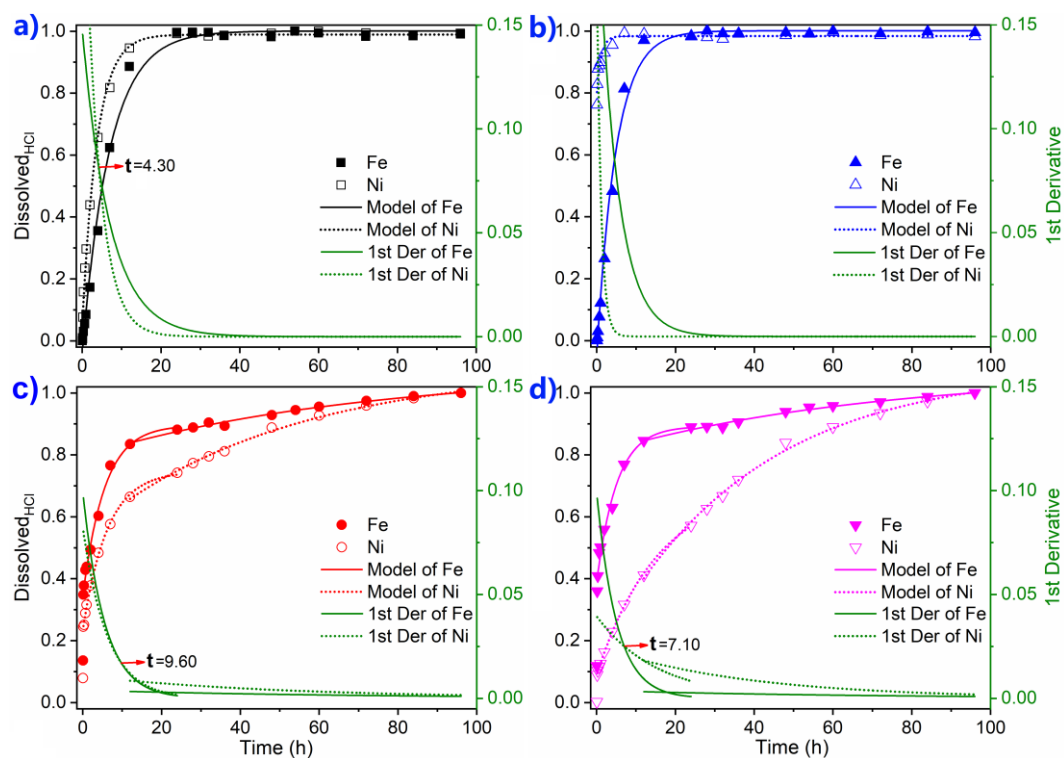


Fig. S7. Modeling of Fe and Ni kinetic release and corresponding 1<sup>st</sup> derivatives during HCl treatment of a) GtNi6, b) GtANi20, c) GtNi6-44d, and d) GtANi20-44d. Fits to the Fe and Ni data are shown as solid and dotted lines, respectively. 1<sup>st</sup> derivative curves are shown as green lines. Red arrows in a), c), and d) indicate the point where the 1<sup>st</sup> derivatives of Fe and Ni release are equal.

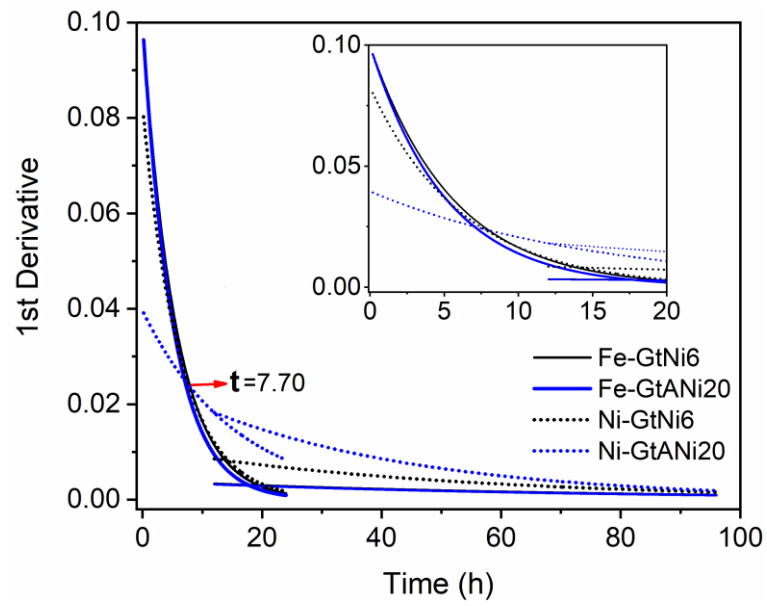


Fig. S8. First derivative of modeled Fe and Ni kinetic release of GtNi6 and GtANi20.

Table S1

Relative contents of Fe-bearing minerals determined from Rietveld refinement of XRD data in pristine Ni-free/-containing goethites and corresponding reaction products after interaction with S(-II).

Sample	Time	Goethite	Pyrite	Greigite	Mackinawite
		f%	f%/f <sub>S</sub> %	f%/f <sub>S</sub> %	f%/f <sub>S</sub> %
Gt	0d	100	-/-	-/-	-/-
	3d	98.1	1.0(2)/-	0.1(1)/-	0.8(1)/-
	7d	61.7(5)	35.8(5)/93.7	0.6(2)/1.5	1.9(1)/4.8
	25d	59.5(5)	38.5(5)/95.1	1.1(2)/2.8	0.9(1)/2.1
	44d	41.5(5)	54.4(5)/92.8	2.8(2)/4.8	1.4(1)/2.4
GtNi2	0d	100	-/-	-/-	-/-
	3d	97.4	1.6(1)/-	0.2(1)/-	0.8(1)/-
	7d	70.9(5)	27.5(5)/94.6	0.4(1)/1.5	1.1(1)/3.9
	25d	57.8(6)	37.7(5)/89.4	3.3(2)/7.8	1.2(1)/2.8
	44d	54.1(5)	33.2(4)/72.4	9.7(3)/21.2	3.0(1)/6.5
GtNi6	0d	100	-/-	-/-	-/-
	3d	97.9	1.4(1)/-	-/-	0.7(1)/-
	7d	58.2(7)	39.1(6)/93.5	0.9(2)/2.2	1.8(1)/4.2
	25d	52.0(6)	33.9(5)/70.6	13.2(4)/27.4	1.0(1)/2.0
	44d	53.8(5)	33.5(5)/72.5	11.5(3)/24.8	1.3(1)/2.7
GtANi5	0d	100	-/-	-/-	-/-
	3d	97.8	1.6(1)/-	-/-	0.6(1)/-
	7d	66.0(6)	31.5(5)/92.5	0.8(2)/2.5	1.7(1)/5.0
	25d	57.3(6)	38.2(5)/89.5	3.0(2)/7.0	1.5(1)/3.6
	44d	50.4(6)	33.0(5)/66.6	11.0(3)/22.1	5.6(2)/11.2
GtANi20	0d	100	-/-	-/-	-/-
	3d	99.1	0.5(1)/-	0.3(1)/-	0.1(1)/-
	7d	69.1(5)	29.2(5)/94.6	0.4(2)/1.4	1.2(1)/4.0
	25d	48.5(8)	36.2(8)/70.3	13.9(8)/26.9	1.4(1)/2.8
	44d	47.6(5)	40.7(5)/77.7	3.7(2)/7.0	8.0(2)/15.3

Note: f% represents the mass fraction (wt.%) of a specific mineral in the samples, whereas f<sub>S</sub>% represents the relative proportion of this mineral among iron sulfides (pyrite + greigite + mackinawite).



Table S2

Unit-cell parameters of Fe-bearing minerals in pristine Ni-free/-containing goethites and corresponding reaction products and fit quality parameters of the Rietveld refinement.

Sample	Time	Rwp	$\chi^2$	Goethite			Pyrite	Greigite	Mackinawite	
				a	b	c	a	a	a	c
Gt	0d	2.05	1.27	4.629(5)	9.957(6)	3.025(2)	--	--	--	--
	3d	2.33	1.24	4.626(9)	9.958(10)	3.023(3)	5.435(12)	9.975	3.697(42)	5.083(66)
	7d	3.22	2.35	4.629(9)	9.964(12)	3.025(4)	5.427(5)	9.975	3.698(19)	5.083
	25d	3.75	1.42	4.630(12)	9.964(16)	3.025(5)	5.430(6)	9.922(47)	3.710	5.083
	44d	3.10	2.08	4.631(8)	9.963(11)	3.024(3)	5.429(4)	9.884(18)	3.662(23)	5.072(34)
GtNi2	0d	2.56	1.42	4.624(7)	9.966(8)	3.027(2)	--	--	--	--
	3d	2.49	1.21	4.619(8)	9.959(10)	3.022(3)	5.432(8)	9.953(28)	3.680(37)	5.083
	7d	3.00	1.98	4.620(10)	9.962(13)	3.023(4)	5.431(6)	9.975	3.704(27)	5.083
	25d	3.50	1.90	4.628(10)	9.968(13)	3.024(4)	5.433(5)	9.890(19)	3.672(31)	5.078(46)
	44d	2.90	2.06	4.622(7)	9.961(9)	3.023(2)	5.429(3)	9.872(17)	3.668(7)	5.050(15)
GtNi6	0d	2.22	1.31	4.624(5)	9.967(6)	3.026(2)	--	--	--	--
	3d	2.47	1.37	4.624(7)	9.965(9)	3.024(3)	5.435(8)	--	3.710	5.083
	7d	3.33	2.10	4.625(13)	9.975(18)	3.026(5)	5.439(6)	9.975	3.685(21)	5.083
	25d	2.88	1.90	4.621(8)	9.966(11)	3.022(3)	5.433(4)	9.875(17)	3.692(22)	5.083
	44d	2.70	1.70	4.622(7)	9.967(10)	3.023(3)	5.433(3)	9.879(14)	3.660(17)	5.063(26)
GtANi5	0d	2.08	1.17	4.629(4)	9.956(5)	3.025(1)	--	--	--	--
	3d	2.27	1.20	4.624(7)	9.955(9)	3.023(3)	5.425(7)	--	3.710	5.083
	7d	3.15	2.07	4.625(9)	9.961(12)	3.024(3)	5.433(6)	9.975	3.695(23)	5.083
	25d	3.13	1.76	4.630(9)	9.967(14)	3.025(3)	5.435(5)	9.907(20)	3.666(23)	5.083
	44d	2.79	1.67	4.624(8)	9.962(10)	3.023(3)	5.432(4)	9.877(13)	3.670(5)	5.045(10)
GtANi20	0d	2.12	1.23	4.629(4)	9.956(5)	3.025(1)	--	--	--	--
	3d	2.13	1.11	4.626(7)	9.960(8)	3.025(2)	5.440(14)	9.783(110)	3.710	5.083
	7d	2.96	1.95	4.628(10)	9.968(13)	3.026(4)	5.439(6)	9.975	3.710	5.083
	25d	3.18	1.95	4.633(10)	9.965(15)	3.025(4)	5.438(5)	9.887(76)	3.683(23)	5.049(36)
	44d	3.15	1.84	4.624(8)	9.960(11)	3.023(3)	5.432(4)	9.883(14)	3.672(4)	5.047(10)

Table S3

Kinetic parameters computed for Fe ( $y_1$ ) and Ni ( $y_2$ ) release from solids in HCl solutions.

Acid Treatment		HCl	
Time		0.167-24 h	24-96 h
GtNi6		$y_1 = -1.04 * e^{-t/7.02} + 1.00, r^2 = 0.9957;$ $y_2 = -0.94 * e^{-t/3.75} + 0.99, r^2 = 0.9970;$	
GtANi20		$y_1 = -1.05 * e^{-t/4.90} + 1.00, r^2 = 0.9955;$ $y_2 = -0.20 * e^{-t/1.09} + 0.98, r^2 = 0.9346;$	
GtNi6-44d		$y_1 = -0.55 * e^{-t/5.55} + 0.90, r^2 = 0.9932;$ $y_2 = -0.51 * e^{-t/6.22} + 0.75, r^2 = 0.9989;$	$y_1 = -0.28 * e^{-t/69.25} + 1.07, r^2 = 0.9888;$ $y_2 = -0.55 * e^{-t/45.94} + 1.07, r^2 = 0.9903;$
GtANi20-44d		$y_1 = -0.51 * e^{-t/5.09} + 0.89, r^2 = 0.9832;$ $y_2 = -0.61 * e^{-t/15.41} + 0.70, r^2 = 0.9993;$	$y_1 = -0.26 * e^{-t/67.69} + 1.06, r^2 = 0.9956;$ $y_2 = -0.93 * e^{-t/37.01} + 1.07, r^2 = 0.9956;$

**References:**

- Ikogou M., Ona-Nguema G., Juillot F., Le Pape P., Menguy N., Richeux N., Guigner J. M., Noel V., Brest J., Baptiste B. and Morin G. (2017) Long-term sequestration of nickel in mackinawite formed by *Desulfovibrio capillatus* upon Fe(III)-citrate reduction in the presence of thiosulfate. *Appl. Geochem.* **80**, 143-154.
- Nöel V., Kumar N., Boye K., Barragan L., Lezama-Pacheco J. S., Chu R., Tolic N., Brown G. E. and Bargar J. R. (2020) FeS colloids - formation and mobilization pathways in natural waters. *Environ. Sci. Nano* **7**, 2102-2116.